

# Armed Services Technical Information Agency

Because of our limited supply, you are requested to return this copy WHEN IT HAS SERVED YOUR PURPOSE so that it may be made available to other requesters. Your cooperation will be appreciated.

AD  
38648

NOTICE: WHEN GOVERNMENT OR OTHER DRAWINGS, SPECIFICATIONS OR OTHER DATA ARE USED FOR ANY PURPOSE OTHER THAN IN CONNECTION WITH A DEFINITELY RELATED GOVERNMENT PROCUREMENT OPERATION, THE U. S. GOVERNMENT THEREBY INCURS NO RESPONSIBILITY, NOR ANY OBLIGATION WHATSOEVER; AND THE FACT THAT THE GOVERNMENT MAY HAVE FORMULATED, FURNISHED, OR IN ANY WAY SUPPLIED THE SAID DRAWINGS, SPECIFICATIONS, OR OTHER DATA IS NOT TO BE REGARDED BY IMPLICATION OR OTHERWISE AS IN ANY MANNER LICENSING THE HOLDER OR ANY OTHER PERSON OR CORPORATION, OR CONVEYING ANY RIGHTS OR PERMISSION TO MANUFACTURE, USE OR SELL ANY PATENTED INVENTION THAT MAY IN ANY WAY BE RELATED THERETO.

Reproduced by  
DOCUMENT SERVICE CENTER  
KNOTT BUILDING, DAYTON, 2, OHIO

UNCLASSIFIED

AD NO. 38643  
ASTIA FILE COPY

**NAVORD REPORT 2689**

**EVALUATION OF GLASS FABRIC REINFORCED PLASTIC LAMINATES**

**30 JANUARY 1953**



**U. S. NAVAL ORDNANCE LABORATORY**  
**WHITE OAK, MARYLAND**

EVALUATION OF GLASS FABRIC REINFORCED PLASTIC LAMINATES

Prepared by:

F. Robert Barnett

**ABSTRACT:** Use of reinforced plastics as materials of construction for naval ordnance requires that specifications be established to control the quality of these materials. Many such material specifications already exist and are used as a basis for the procurement of plastics. However, further information and exact data are required if these materials are to be properly used and specified in ordnance design. Properties of laminates made with different reinforcements and tested under various environmental conditions peculiar to the ordnance field must be made available.

To provide a limited amount of specialized data, a program of evaluation of numerous materials and process variables on the physical, electrical and mechanical properties of glass cloth laminates was undertaken by the Naval Ordnance Laboratory. Included were the variables of fabric weave, yarn weight, fabric finish, type resin, test panel thickness, resin content, and temperature at the time of test. Test panels were molded under precise conditions, and the properties of the laminates were measured after storage for one week at 75°F and 50% RH. No data were taken after sea water immersion, outdoor exposure or other conditions of service.

U. S. NAVAL ORDNANCE LABORATORY  
WHITE OAK, MARYLAND

30 January 1953

NAVORD Report 2669 presents data on plastic laminates which are necessary for the specification of reinforced plastic materials to be employed in the manufacture of structures for naval ordnance devices. It is believed that they are sufficient for the specification of design models and prototypes. However, concurrent with tests on these units, considerable data must still be gathered on the influence of such factors as sea water immersion, transportation vibration, impact, dead loads, and outdoor exposure and on variable storage temperatures and humidities. These further data are necessary before satisfactory service life can be assured on materials subject to the more stringent environmental conditions. Test panels for the program discussed in this Report were prepared at the Naval Ordnance Laboratory on its precision molding press and were then sent to the Forest Products Laboratory, Madison, Wisconsin, for preparation of the test specimens, testing, and reporting of the data. The work at the Forest Products Laboratory was carried out by K. H. Boller and L. L. Downs, engineers. Excerpts from their report to the Naval Ordnance Laboratory are incorporated in this Report. The work was originated at the request of the Naval Ordnance Test Station, Inyokern, California, and was concluded as authorized by task NOL-Ref-a-268-18-53. The data reported herein are applicable to all those applications where glass fabric reinforced laminated plastics are materials of consideration in the production of ordnance. They do not, however, represent the sum total of the data needed for this purpose.

EDWARD L. WOODYARD  
Captain, USN  
Commander

D. S. MUZZEY, JR.  
By direction

# CONTENTS

	Page
Introduction.....	1
Preparation of Test Panels.....	1
Test Methods.....	2
Discussion of Results.....	3
A. Evaluation of Laminates Made of Fabrics of Different Weaves and Yarn Types.....	3
Conclusions.....	6
A. Group 1. Evaluation of Laminates Made of Fabrics of Different Weaves and Yarn Types.....	6
B. Group 2. Effect of Laminating Conditions on the Strength of Plastics.....	6
C. Group 3. Variation of Strength Properties Because of Evaluation Conditions.....	9

# ILLUSTRATIONS

Tables 1 through 8

Figures 1 through 11

## EVALUATION OF GLASS FABRIC REINFORCED PLASTIC LAMINATES

## INTRODUCTION

1. The program to investigate the properties of glass-fabric-reinforced plastic includes an evaluation of the physical, mechanical, and electrical properties of specific laminates as molded, as well as the effects of a number of variables on these properties.

2. It is the purpose of this investigation to evaluate the properties of laminates made of two resin types, polyester and phenolic; five different glass-fabric weaves; two different types of yarn; two different finishes; four different thicknesses; five different resin contents; and tested at seven different temperatures.

## Preparation Of Test Panels

3. All of the laminates for this investigation were supplied by the Naval Ordnance Laboratory. The panels were all parallel laminated with glass fabrics using either a polyester or phenolic-type resin as follows:

All polyester-resin laminates were made using a wet lay up procedure and an effort was made to eliminate the air from the piece. Six hundred PT Cellophane was used to contain the wet panel. After lay up the Cellophane was sealed with scotch tape, after which the panel was rolled with a steel roller until the air had been eliminated. The entire operation required approximately 1 hour. The panel was then placed in a Baldwin-Southwark precision laminating press and pressure was applied. Approximately 5 hours were required to produce a good solid gel at room temperature. At completion of this preliminary curing condition under pressure, the laminate was removed from the press and placed in an oven operating at 110°F for 24 hours to complete the cure. The resin and catalyst system used was as follows:

Resin: Paraplex P-43 (Rohm and Haas Co.)

Catalyst: 1.25 percent BDM (Methyl ethyl ketone peroxide)

Accelerator: 1.00 percent Nuodex (6 percent) (Cobalt Naphthenate)

All phenolic laminates were made using a dry lay up procedure. The required number of plies of preimpregnated glass cloth were cut and laid in position on Cellophane (600 PT) after which they were sealed in with scotch tape. The piece was then placed in the Baldwin-Southwark precision laminating press and pressure was applied. After the desired pressure had been reached, heat was applied to the platens and the piece was maintained at a temperature of 300° ± 5°F for 1 hour to effect cure. At the end of this heating period the press was cooled to ambient temperature and the panel was removed. The impregnated cloths had the following characteristics before cure:

\*Phenolic impregnated glass cloth was treated by Fabrickon Products, Inc.,  
Plastics Division, Silver Range, Michigan

Resin: Bakelite BV 17085  
 Resin content: Approximately 35 percent  
 Volatile matter: 6-1/2 percent volatile matter (determined by  
 10-minute exposure at 160°C)

Further molding data are given in Table 1.

#### Test Methods

4. The test procedures, in general, conformed to the methods specified in Federal Specification for Plastics, Organic: General Specifications, Test Methods, No. L-P-406a and amendments thereto. The following mechanical, physical, and electrical tests were made on the specimens from each of the panels referred to in Table 1.

##### Mechanical tests

Tension - Method 1011  
 Compression - Method 1021  
 Flexure - Method 1031  
 Shear (double) - Method 1041  
 Izod impact - Method 1071

##### Physical tests

Water Absorption - Method 7031  
 Dimensional change - Method 7031  
 Specific gravity - Method 5012

Resin content <sup>2</sup>

##### Electrical properties

Power factor <sup>3</sup>  
 Dielectric constant <sup>3</sup>

5. The specimens for the mechanical and physical tests were cut from the panels by means of a carborundum saw, and when further shaping was necessary, a fine emery wheel on a vertical spindle was used. The specimens so machined were stored for at least a week prior to test at 75°F ± 2°F,

---

<sup>2</sup> L-P-406a has no method so USAF Specification 12049, paragraph F-6b(4) was used.

<sup>3</sup> The dielectric constant and power factor were determined at a frequency of 8,530 megacycles per second, by use of a "Microwave Dielectrometer", Model 2, manufactured by Central Research Laboratories, Inc., Red Wing, Minnesota. Actually the loss tangent was determined, rather than power factor, but for low-loss materials such as these plastic laminates the difference between loss tangent and power factor does not exceed 3 units in the fifth decimal place, which is less than the experimental error or the error introduced by rounding off the results to four decimal places.



50  $\pm$  2 percent relative humidity. Mechanical test specimens in Group 3 were held at the test temperature for 1/2 hour before test. Temperature measurements with a thermocouple showed that the test temperature was attained after 10 minutes exposure; however, an additional 20 minutes was allowed before testing. The specimens for the electrical tests were roughly shaped on a Deall band saw and then finally shaped with machine tools and emery paper.

## Discussion Of Results

### A. Evaluation of Laminates Made of Fabrics of Different Weaves and Yarn Types

#### Variations in Fabrics

6. General. The investigation was concerned with the variation in physical, mechanical, and electrical properties of laminates made with fabrics of different weaves. Five cloth styles which included three types of weaves were investigated.

7. Resin content. The resin contents of the polyester-type laminates are greater than those of the phenolic type having resin contents which range from 32.7 to 44.7 percent as compared with the phenolic-type laminates which range from 22.3 to 29.3 percent. A comparison of the laminate with 114 finish shows that the 128-type fabric has the highest resin content in its particular resin class. In each resin class there is a duplication of panels made with 161-114-225 fabric. The resin contents of these duplicate panels are very nearly equal.

8. Specific gravity. The majority of the panels in Group 1 have specific gravities which vary from 1.685 to 1.910 (Table 2, Column 4). There are two panels, however, (panels 1.2 and 1.6, Table 1) which are considerably below this range. Both of them were made of phenolic resin, one with 128-114 and the other with 164-114 fabric. Except for these two panels, the values are within the range usually found in glass-fabric-base laminates. It was found, however, that duplicate panels made of these two fabrics and phenolic resin had about the same specific gravities as those tabulated so it was concluded that this low specific gravity was because of insufficient resin on the fabric thus allowing too little compression of the plies in the fabrication technique employed.

9. Water absorption and dimensional change. There were considerably more pores or voids in the laminates (panels 1.2 and 1.6) having low specific gravity than in the other laminates, which were void-free. This fact accounts for the high values of water absorption for these two panels (Table 2, Column 5). A comparison of values shows that the water absorption of laminates fabricated with polyester resin is under 0.14 percent and that the values from phenolic laminates are over 0.62 percent.

10. Table 2, Columns 6 to 8, which presents the dimensional change due to water absorption shows that the greatest change is 0.52 percent. The small values are typical of glass-fabric-base laminates.



11. Compression, shear, and Izod impact strengths. Figure 1 also shows graphically the average strength values for compression, shear, and Izod impact. Since all of the panels were parallel laminated, these strength values show the relative strengths at  $0^\circ$  and  $90^\circ$  to the warp. The 143-144 fabric is, of course, the strongest of the fabrics in the  $0^\circ$  direction and the weakest in the  $90^\circ$  direction. The other fabrics are not so unidirectional. The laminates made with 181-type fabric have higher strength values in compression and shear than do the other laminates tested but are weaker in impact strength. The compressive and shear strengths of a given fabric fabricated with phenolic resin are generally lower than for the same fabric laminated with a polyester; however, the reverse is true of their impact strengths. The laminates having voids, that is, the 128 and 164 fabrics having phenolic resin binder, are definitely weaker in all properties.

12. Tension. The tensile properties of the various glass-fabric-base laminates, as shown in Group 1 of Table 3, are listed under two major headings, modulus of elasticity and stress. These values serve to define an average stress-strain curve for the material in question. Such an average curve has been reproduced (Figure 2) for each material in its two principal directions. A comparison of these stress-strain curves shows that the 143 fabric is highly unidirectional and that even though all panels were parallel laminated, the  $0^\circ$  and  $90^\circ$  properties of the other laminates are nearly equal. The proportional limit values of all the laminates are a small percentage of the maximum stress. The meaning of this low value is questionable since the portion of the stress-strain curve above it is also a straight line for most of the materials. There was, however, a definite break at this point for most of the materials. Previous experiments have shown that if these materials are prestressed beyond the apparent initial proportional limit, a new modulus of elasticity and proportional limit are established.<sup>4</sup> The new modulus of elasticity has a lower value than the first one and might be about equal to the second straight line or a secant modulus, depending on the amount of prestressing. For this reason, the secant modulus at 0.2 percent strain offset has been computed. Secant modulus at 0.2 percent strain offset was not obtainable for all materials so that the secant modulus at 0.1 percent strain offset was also computed.

13. The laminates which had the lowest strength are again those which were made of phenolic resin and either 128 or 164 fabric. These laminates contained voids which caused poor bonds between the laminations of fabric. The fracture of specimens from these laminates was a splintering, brooming type, which delaminated from the break toward the grip. The void-free specimens had, in general, cleaner breaks across the net section.

14. Flexure. The results of the flexural tests, Group 1 of Table 5, show strength values comparable to those shown for the tensile tests. The flexural properties, however, show higher proportional-limit values and the average load-deflection curves (Figure 3) do not exhibit dual

---

<sup>4</sup> Werren, Fred, Effect of Prestressing in Tension or Compression on the Mechanical Properties of two Glass-fabric-base Plastic Laminates. Forest Products Laboratory Report No. 1811. September 1950.

straight lines. The flexural stresses, being a combination of tension and compression stresses show by a detailed comparison about the same relation among materials as the tensile tests.

15. Electrical properties. Any variation in electrical properties attributable to variations in fabrics was too small to be detected in the presence of the normal experimental errors.

### Series 2. Variations in Yarns

16. Series 2 of this investigation deals with variations in the physical, mechanical, and electrical properties resulting from a variation in yarn "count", which is an indication of the number of yards of basic strand per pound of yarn. The evaluation of these properties was obtained from panels made of 181-114 fabric with both polyester and phenolic-type resin. The yarn count of one set of panels was 150 (15,000 yards of basic filament per pound) and that of the second set was 225 (22,500 yards of basic filament per pound).

17. The results show that a difference in yarn count did not greatly affect the specific gravity, percentage water absorption, ultimate compressive strength, or flexural strength of laminates made with either type of resin. Neither did this difference significantly affect either the flatwise shear strength of polyester-type laminates or the Izod impact and tensile strengths of the phenolic-type laminates. This difference in yarn count seemed to affect only the flatwise shear strength of the phenolic-type laminate and the Izod impact and tensile strengths of the polyester-type laminate. These strengths were affected to the extent that the laminate with 150-count yarn was stronger in impact and tension but weaker in shear.

18. Electrical properties. No variations in electrical properties due to variations in yarn count could be detected, because if present, they are smaller than experimental error and variations attributable to differences in resin content.

### Series 3. Variations in Finish

19. The evaluation of the effects of different fabric finishes on the properties was obtained from laminates made with both polyester and phenolic-type resins in combination with the 181-136 fabric for comparison with those obtained from laminates made of 181-114-225 fabric. The results of the physical tests show that the specific gravities of the laminates with 136-type finish are less than those with 114-type finish. The phenolic laminate with 136 finish contained some voids which caused greater water absorption and dimensional changes than were experienced in either the polyester laminate or the laminate with 114 finish and phenolic resin. It should be noted that the 136-type finish was intended primarily to improve the wet strength of a laminate but wet strength tests were not a part of this evaluation. The results of the dry strength tests show, however, that the 136-type finish with polyester-type resin had compressive, shear, tensile, and flexural strengths equal to or less than the 114-type finish. The Izod impact strength showed a slight improvement.

All of the strengths, however, from the phenolic panel with 136 finish were less than those with 114 finish. Some of this deficiency may be a result of the low specific gravity.

20. Electrical properties. Any effect of variations in finish on electrical properties was small, and negligible in comparison to the effects of resin content and the normal experimental error inherent in determinations of this kind.

#### B. Group 2. Effect of Laminating Conditions on the Strength of Plastics

21. General. The evaluation of the effect of certain laminating and fabricating conditions on properties of glass-fabric-base plastics was conducted on one combination of materials, 181-114-225 fabric plus a polyester-type resin. This evaluation includes (1) the fabrication variable of thickness and (2) the combined effect of varying the resin content and pressure during fabrication. To evaluate these effects, the same physical, mechanical, and electrical tests were conducted on laminates in Group 2 as were conducted on laminates in Group 1.

22. Resin content. The resin content of the panels in Series 5 varies from 21.8 to 41.6 percent. The desired range for this series was from 20 to 50 percent which was to be accomplished by a pressure variation from 395 to 2 pounds per square inch. The 2 pounds per square inch pressure, however, resulted in 39.5 instead of 50 percent resin content. It may be noted also that the 61 pounds per square inch laminating pressure (panels 1.7 and 1.9) resulted in a 33.2 percent resin content which is greater than the 30.0 percent resulting from a pressure of 45 pounds per square inch, all of which means that the resin content is dependent upon factors other than pressure.

23. Specific gravity. As the resin content increases, the specific gravity decreases, which is as expected, since glass is heavier than resin.

24. Water absorption and dimensional stability. A comparison of the water absorption values as shown in Table 2, Column 5, indicates that the percentage of water absorbed increases when the thickness of the laminate is decreased. The values range from 0.05 percent for 1/2-inch-thick material to 0.22 percent for 1/16-inch-thick material.

25. It appears, by a comparison of values on Series 5, that the resin content has little effect on the water absorption except that at 21.8 percent resin content the percentage is higher than normal, with a value of 0.36 percent.

26. The values for dimensional change appear to be unaffected by size or resin content as shown by Table 2, Columns 6 to 8 for Series 4 and 5.

27. Compression, shear and Izod impact strengths. The effects that laminating conditions have on the compression, shear, and Izod impact strength are shown in Figure 4. Even though the strength of these laminates may be affected by their molding pressure as well as by their resin contents, the combination of these effects is shown plotted as a function of resin content only.

23. This visual comparison of values and those presented in Tables 4, 6, and 7 shows the following trends:

a. The edgewise compressive strength increases with increases in thickness from 1/16 inch to 1/4 inch; the strength of the 1/2-inch-thick laminate is about the same as that of the 1/4-inch laminate.

b. The flatwise shear strength of these laminates shows very little increase in strength with increases in thickness.

c. The edgewise Izod impact strength also increases with increase in thickness, having values of about 11 foot-pounds per inch of width at 1/8 inch and 17 foot-pounds at 1/2 inch of thickness.

d. The edgewise compressive strength appears unaffected by resin content.

e. The flatwise shear strength decreases slightly with increase in resin content.

f. The edgewise Izod impact strength decreases with increase in resin content.

29. Tension. Figure 5 presents graphically the results of tensile tests, which are tabulated in Table 3, to show the effect of laminating conditions on tensile properties of plastics. This figure shows that both the maximum tensile strength and the secant modulus at 0.2 percent strain offset are reduced by an increase in resin content. The tensile strength decreases from 53,000 pounds per square inch at 21.8 percent resin content to 29,380 pounds per square inch at 41.6 percent resin content or about 1,250 pounds per square inch change in stress per percent change in resin content. The secant modulus decreases about 37,000 pounds per square inch per percent change in resin content.

The proportional limit stress appears to be unaffected by either resin content or thickness of the laminate. Due to the scatter of points, it is difficult to determine the trend indicated by the points for effect of thickness on secant modulus or maximum tensile strength, although there is some indication that tensile strength increases with increasing thickness.

30. Flexure. The results of the flexural tests as shown on Figure 6 indicate decreases in modulus of rupture and secant modulus as a result of increases in either thickness or resin content. Slight increases in compressive and tensile strength were observed with increases in thickness, yet these flexure tests show a decrease in strength with increases in thickness. The decrease in modulus of rupture with increase in resin content is in agreement with the tensile test results.

31. Electrical properties. No effect of panel thickness on dielectric constant and power factor was discernible.

32. The dielectric constant of the polyester laminates had a striking relation to their resin content, as illustrated in Figure 10. The dielectric constant decreased as the resin content increased, which would be expected if the dielectric constant of glass is higher than that of the polyester resin. There is a certain amount of scattering of the points, but it appears that the resin content - dielectric constant curve follows an approximately straight line over the range investigated.

33. The power factor of the polyester laminates was approximately constant over the range of resin content investigated, suggesting that the power factor of the polyester resin may be approximately equal to that of the glass used. The power factor of panel 4.3 appears very low (and a low power factor is desirable) but this may not indicate a real superiority of this panel in this respect. The data on this panel turned out in such a way that in the course of calculation of power factor most data were not usable because they were outside the range of certain curves used for calculation purposes, hence the figure reported is one single value rather than the average of several, and it is believed to be too low.

34. The points for dielectric constant and power factor of the phenolic resin laminates would be crowded both on Figures 10 and 11, and there appears to be little relation between resin content and electrical properties. No attempt was made, therefore, to plot the points but instead a circle was drawn on each figure, which would enclose all points for phenolic laminates except a few representing panels of abnormally low specific gravity and which in some cases contained voids.

35. If a low dielectric constant and power factor are considered desirable, then of the materials tested all polyester laminates tested having resin contents of 30 percent or over were superior to the phenolics in respect to dielectric constant, and all polyester panels regardless of resin content were superior to the phenolics in power factor.

36. From the results on both polyester and phenolic laminates, it appears that a certain weight or percentage of glass has a certain effect on electrical properties, irrespective of the manner in which the glass is present (weave, yarn count, finish).

#### C. Group 3. Variation of Strength Properties Because of Evaluation Conditions

37. General. The third group of tests was conducted to determine the effect of a specific evaluation condition -- temperature at the time of test. Mechanical tests were conducted on test specimens at temperatures of -65°F, -30°F, 0°F, 30°F, 75°F, 120°F and 160°F. Specimens were held at the respective temperatures for 1/2 hour before test. Physical and electrical tests were, however, conducted at room temperature. Average values of strengths obtained are shown on the various tables. These values are shown also in Figures 7, 8, and 9.

38. Physical properties. The results of the physical tests, as shown in Table 2 for Group 3, which were obtained at room temperature, show how nearly identical the panels are to each other. The panels having polyester-type resin, for example, have resin contents between 30.0 and 36.4 percent. The pair of control panels in Group 1 had resin contents of 33.4 and 33.7 percent, respectively. The panels having phenolic-type resin show even less variation — the range is 23.3 to 23.9 percent. The specific gravity and water absorption values in Table 2 also show a uniformity of results.

39. Mechanical properties. All of the mechanical tests in Group 3 may be discussed together because they show the same trend. The data on Figures 7, 8, and 9 show that for increases in temperature from -65°F to 160°F there is a decrease in strength. That decrease in strength is greater for the laminates having polyester-type resin than for the laminates having phenolic-type resin. The trends are shown by broken lines through the scattered points. The scatter is, of course, due to the method of matching the specimens in this series of tests. Each point represents the average value from five specimens from a given panel so that the scatter includes the variation between panels. The trends, however, are well defined, except for tensile stress below maximum. The stresses at intermediate points on the stress-strain curve in tension show no trend (Table 3, Group 3, Column 7) or slight upward trends (Columns 8 and 9 or Figure 8). No particular significance is attached to this behavior because the initial tangent modulus (Column 4) decreases with increases in temperature the same as the other strength properties. This decrease in modulus indicates a flatter initial slope and hence a greater strain and stress at the 0.1 or 0.2 percent strain offset than experienced at the low temperatures.



## CONCLUSIONS

### A. Group 1. Evaluation of Laminates Made of Fabrics of Different Weaves and Yarn Types

40. The tables and charts show major differences among the materials such as: (1) The unidirectional property of 143 weave; (2) the detrimental effect of voids and low specific gravity; and (3) the small change in strength due to a difference in yarn type. The effect of 136-type finish is not conclusive because of the low glass content of the panels tested.

41. The results show also the reproducibility of values from two identical panels. This reproducibility may be seen by comparing the values in Series 1 obtained from panel 1.7 with those of 1.9 or the values obtained from panel 1.8 with those of 1.10. The average test values obtained from identical panels are in such close agreement that they were averaged to give a value which represents the strength for that particular combination of materials. This representative value was then used for comparative purposes in each series which followed.

42. Electrical properties. The dielectric constant and power factor appeared to be affected little, if any, by variations in fabrics, yarn count, or finish. Any differences in these electrical properties that may have resulted from variations in these factors were so small that they are within the limits of experimental error.

### B. Group 2. Effect of Laminating Conditions on the Strength of Plastics

43. The data obtained in Group 2 show that the fabrication variables, thickness and resin content, do affect the mechanical properties. Tests of laminates which varied in thickness from 1/16 to 1/2 inch indicate that increases in thickness caused increases in the compression, shear, Izod impact, and tensile strength. Flexural strength was the only one which showed a decrease. Tests of laminates which varied in resin content from 21.8 to 41.6 percent showed that the shear, tensile, flexural, and Izod impact strengths decrease with increases in resin content. The compressive strength appeared to be unaffected by resin content.

### C. Group 3. Variation of Strength Properties Because of Evaluation Conditions

44. The results show that the strength of glass-fabric-base laminates fabricated with either a polyester- or phenolic-type resin decreases with increases in temperatures at time of test; also, that those with polyester-type resin decrease more than those with phenolic-type resin. The exact amounts of these decreases vary with the mechanical test. The amounts are shown in the tables for particular applications.



Table 1.—Fabrication methods used in making laminated panels of glass fabric with typical polyester and phenolic resins

Panel No.	Resin <sup>1</sup> type	Type of glass fabric <sup>2</sup>	Number of plies <sup>3</sup>	Thickness in inches <sup>4</sup>	Cure cycle Time: Temp.: Pressure:
Naval Ordnance Laboratory	F.P.L.				
				In.	Hr.: °F.: P.s.i.

## GROUP 1.— VARIATIONS IN FABRICS

## Series 1 — Variations in Weaves

269GP12131	: 1.1	: Polyester	: 128-114	: 18	: .0127	: 5	: 75	: 10
	:	:	:	:	:	: 24	: 110	: 0
269GP1472	: 1.3	: .....do.....	: 143-114	: 14	: .0146	: 5	: 75	: 6
	:	:	:	:	:	: 24	: 110	: 0
269GP1373	: 1.5	: .....do.....	: 164-114	: 9	: .0137	: 5	: 75	: 5
	:	:	:	:	:	: 24	: 110	: 0
269GP1396	: 1.7	: .....do.....	: 181-114-225	: 15	: .0139	: 5	: 75	: 61
	:	:	:	:	:	: 24	: 110	: 0
269GP1397	: 1.9	: .....do.....	: 181-114-225	: 15	: .0142	: 5	: 75	: 61
	:	:	:	:	:	: 24	: 110	: 0
269GP12129	: 1.11	: .....do.....	: 182-114	: 10	: .0131	: 5	: 75	: 16
	:	:	:	:	:	: 24	: 110	: 0
269GB13144	: 1.2	: Phenolic	: 128-114	: 19	: .0136	: 1	: 300	: 10
269GB13142	: 1.4	: .....do.....	: 143-114	: 15	: .0136	: 1	: 300	: 7
269GB14146	: 1.6	: .....do.....	: 164-114	: 9	: .0144	: 1	: 300	: 5
269GB12140	: 1.8	: .....do.....	: 181-114-225	: 15	: .0128	: 1	: 300	: 37
269GB 12141	: 1.10	: .....do.....	: 181-114-225	: 15	: .0127	: 1	: 300	: 37
269GB12145	: 1.12	: .....do.....	: 182-114	: 10	: .0130	: 1	: 300	: 20

## Series 2 — Variations in Yarns

269GP1395	: 2.1	: Polyester	: 181-114-150	: 15	: .0137	: 5	: 75	: 61
	:	:	:	:	:	: 24	: 110	: 0
269GB13143	: 2.2	: Phenolic	: 181-114-150	: 15	: .0131	: 1	: 300	: 37

NAVORD Report 2669

Table 1.--Fabrication methods used in making laminated panels of glass fabric with typical polyester and phenolic resins (Continued)

Panel No.	Resin <sup>1</sup> type	Type of glass <sup>2</sup> fabric <sup>2</sup>	Number of plies <sup>2</sup>	Thick- ness <sup>2</sup>	Cure cycle
Naval : F.P.L. :	:	:	:	:	Time: Tem- : Pres-
Ordinance :	:	:	:	:	para- sure
Laboratory :	:	:	:	:	ture :
:	:	:	:	In. : Hr. : °F. : P.s.i.	:

Series 3 -- Variations in Finish

269GP12149	: 3.1	: Polyester	: 181-136	: 15	: .0.179	: 5	: 75	: 61
:	:	:	:	:	:	: 24	: 110	: 0
269GP12154	: 3.2	: Phenolic	: 181-136	: 15	: .163	: 1	: 300	: 40

Group 2 -- VARIATIONS IN FABRICATION PROCEDURE

Series 4 -- Variation in Thickness

269GP5394	: 4.1	: Polyester	: 181-114-225	: 64	: .532	: 5	: 75	: 61
:	:	:	:	:	:	: 24	: 110	: 0
269GP2675	: 4.3	: ....do.....	: 181-114-225	: 32	: .266	: 5	: 75	: 61
:	:	:	:	:	:	: 24	: 110	: 0
269GP0674	: 4.5	: ....do.....	: 181-114-225	: 8	: .066	: 5	: 75	: 61
:	:	:	:	:	:	: 24	: 110	: 0

Series 5 -- Variation in Molding Pressure and Resin Content

269GP11132	: 5.1	: Polyester	: 181-114-225	: 10	: .111	: 5	: 75	: 2
:	:	:	:	:	:	: 24	: 110	: 0
269GP12103	: 5.3	: ....do.....	: 181-114-225	: 12	: .130	: 5	: 75	: 10
:	:	:	:	:	:	: 24	: 110	: 0
269GP11104	: 5.5	: ....do.....	: 181-114-225	: 14	: .119	: 5	: 75	: 45
:	:	:	:	:	:	: 24	: 110	: 0
269GP13130	: 5.7	: ....do.....	: 181-114-225	: 17	: .136	: 5	: 75	: 395
:	:	:	:	:	:	: 24	: 110	: 0

Table 1.--Fabrication methods used in making laminated panels of glass fabric with typical polyester and phenolic resins (Continued)

Panel No.	Resin <sup>1</sup> type	Type of glass fabric <sup>2</sup>	Number of plies <sup>3</sup>	Thick- ness <sup>4</sup>	Cure cycle Time: Tem- : Pres- : para- : sure : ture :
Naval : F.P.I. :	:	:	:	:	:
Ordnance :	:	:	:	:	:
Laboratory :	:	:	:	:	:
:	:	:	:	In. : Hr. : °F. : P.S.I.	:

## GROUP 3 -- VARIATIONS IN EVALUATION CONDITIONS

Series 6 -- Variation in Temperature at Time of Test<sup>5</sup>

269GPI3133	: 6.1	: Polyester	: 181-114-225	: 15	: 0.138	: 5	: 75	: 61
:	:	:	:	:	:	:	: 24	: 110 : 0
269GPI3100	: 6.3	: .....do.....	: 181-114-225	: 15	: .141	: 5	: 75	: 61
:	:	:	:	:	:	:	: 24	: 110 : 0
269GPI398	: 6.5	: .....do.....	: 181-114-225	: 15	: .132	: 5	: 75	: 61
:	:	:	:	:	:	:	: 24	: 110 : 0
269GPI3102	: 6.7	: .....do.....	: 181-114-225	: 15	: .135	: 5	: 75	: 61
:	:	:	:	:	:	:	: 24	: 110 : 0
269GPI4101	: 6.9	: .....do.....	: 181-114-225	: 15	: .145	: 5	: 75	: 61
:	:	:	:	:	:	:	: 24	: 110 : 0
269GPI399	: 6.11	: .....do.....	: 181-114-225	: 15	: .136	: 5	: 75	: 61
:	:	:	:	:	:	:	: 24	: 110 : 0
269GB12139	: 6.2	: Phenolic	: 181-114-225	: 15	: .127	: 1	: 300	: 37
269GB12138	: 6.4	: .....do.....	: 181-114-225	: 15	: .125	: 1	: 300	: 37
269GB12137	: 6.6	: .....do.....	: 181-114-225	: 15	: .126	: 1	: 300	: 37
269GB12136	: 6.8	: .....do.....	: 181-114-225	: 15	: .126	: 1	: 300	: 37
269GB12135	: 6.10	: .....do.....	: 181-114-225	: 15	: .125	: 1	: 300	: 37
269GB12134	: 6.12	: .....do.....	: 181-114-225	: 15	: .127	: 1	: 300	: 37

<sup>1</sup> Polyester resin was Paraplex P-43 (Catalyst System of 1.25 percent DDM and 1 percent Nuodex). Phenolic resin was Bakelite BVI7085.

<sup>2</sup> Detailed descriptions of fabrics in U. S. Air Force Specification No. 12051.

<sup>3</sup> Plies parallel laminated for approximate 1/8-inch thickness except series 4 which has 1/2-, 1/4-, and 1/16-inch thicknesses for 64, 32, and 8 ply constructions, respectively.

<sup>4</sup> Average of 30 measurements.

<sup>5</sup> The temperatures at time of test are listed on subsequent tables where the effect of temperature on the properties is shown.

# NAVORD Report 2669

Table 2.--Physical properties of glass fabric-base plastic laminates

F.P.L. panel No.	Factors Investigated	Resin content <sup>1</sup>	Specific gravity <sup>2</sup>	Water absorption <sup>3</sup>	Increase in dimensions due to water absorption <sup>2</sup>		
					Length	Width	Thickness
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)
		Percent		Percent	Percent	Percent	Percent
GROUP 1 -- VARIATIONS IN FABRICS							
Series 1 -- Variations in Weaves							
1.1	128-114 - polyester	38.1	1.815	0.13	-0.04	0.00	0.26
1.3	143-114 - polyester	37.2	1.805	.07	-.09	.00	.00
1.5	164-114 - polyester	38.1	1.805	.14	-.09	.03	-.24
1.7	181-114-225 - polyester	33.4	1.892	.09	-.03	.00	-.24
1.9	181-114-225 - polyester	33.7	1.878	.09	.03	.03	-.47
1.11	182-114 - polyester	32.7	1.910	.10	-.01	-.03	-.51
1.2	128-114 - phenolic	29.3	1.485	1.57	-.02	.13	.25
1.4	143-114 - phenolic	24.5	1.733	.74	.01	.05	.00
1.6	164-114 - phenolic	24.8	1.410	2.29	.04	.03	.13
1.8	181-114-225 - phenolic	23.2	1.815	.94	.02	.07	.00
1.10	181-114-225 - phenolic	24.5	1.848	.62	.03	.00	.26
1.12	182-114 - phenolic	22.7	1.726	.81	.04	.00	.52
Series 2 -- Variations in Yarns							
2.1	181-114-150 - polyester	33.1	1.893	.13	-.03	.00	.00
2.2	181-114-150 - phenolic	22.3	1.811	.71	.00	.02	.00
Series 3 -- Variations in Finish							
3.1	181-136 - polyester	44.7	1.758	.14	.00	.00	.00
3.2	181-136 - phenolic	36.5	1.665	1.57	.02	.10	.61
GROUP 2 -- VARIATIONS IN FABRICATION PROCEDURE							
Series 4 -- Variation in Thickness							
4.1	1/2 inch	27.0	1.975	.05	-.04	.03	.00
4.3	1/4 inch	28.3	1.957	.09	.00	.00	.00
4.5	1/16 inch	27.9	1.987	.22	-.02	.03	.00
Series 5 -- Variation in Molding Pressure and Resin Content							
5.1	2 p.s.i.	39.5	1.756	.15	-.01	-.05	.00
5.3	10 p.s.i.	41.6	1.786	.13	-.01	.00	-.13
5.5	45 p.s.i.	30.0	1.936	.17	-.01	.00	.00
5.7	395 p.s.i.	21.8	2.038	.36	-.02	.00	.00
GROUP 3 -- VARIATIONS IN EVALUATION CONDITIONS							
Series 6 -- Variation in Temperature at Time of Test							
6.1	-65° F.	32.1	1.916	.12	.03	.00	.00
6.3	-30° F.	33.3	1.880	.12	.03	.00	.00
6.5	0° F.	30.0	1.908	.13	.00	.03	.00
6.7	30° F.	31.5	1.912	.16	.03	.00	.00
6.9	120° F.	36.4	1.878	.14	.01	.02	.12
6.11	160° F.	32.1	1.912	.13	.00	.02	.00
6.2	-65° F.	23.6	1.822	.69	.08	.07	.60
6.4	-30° F.	23.6	1.855	.66	.04	.05	.33
6.6	0° F.	23.5	1.859	.83	.04	.00	.40
6.8	30° F.	23.8	1.840	.75	-.01	.02	.13
6.10	120° F.	23.3	1.857	.75	.00	.03	.00
6.12	160° F.	23.9	1.840	.96	-.01	.05	.40

<sup>1</sup>Determined by burning as described in paragraph F-6b(4) of U. S. Air Force Specification 12049. Average of two specimens.

<sup>2</sup>Weight and dimensions taken on each 17- by 22-inch panel.

<sup>3</sup>Weights and dimensions taken according to Method 7031 of Federal Specification L-P-406a. Length of specimen was parallel to warp direction. Average of three specimens.

# NAVORD Report 2669

Table 3.--Results of tensile tests of glass-fabric-base plastic laminates

F.P.L. panel No.	Factors investigated	Relation	Modulus of elasticity			Stress at -			
		of loaded:	direction:			0.1 per-	0.2 per-	Maximum	
		to warp	tangent:	Secant at:	Secant at:	Proportional limit	strain	strain	
			cent	0.1 per-	0.2 per-	cent	offset	offset	
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)
		Degrees	1,000	1,000	1,000	1,000	1,000	1,000	1,000
			P.S.I.	P.S.I.	P.S.I.	P.S.I.	P.S.I.	P.S.I.	P.S.I.

## GROUP 1 -- VARIATIONS IN FABRICS

### Series 1 -- Variations in Weaves

1.1	128-114 - polyester	0	4,120	3,237	3,008	9.98	19.46	26.81	47.23
		90	2,382	2,116	2,016	11.56	20.80	26.50	41.65
1.3	143-114 - polyester	0	4,370	4,112	.....	40.35	70.35	.....	78.52
		90	1,718	1,329	1,103	4.45	5.88	6.11	9.64
1.5	164-114 - polyester	0	2,758	2,361	2,216	6.76	17.03	22.60	35.67
		90	2,271	2,002	1,870	8.79	15.76	20.15	29.94
1.7	161-114-225 - polyester	0	3,315	2,936	2,781	11.66	22.33	30.96	41.24
		90	2,922	2,510	2,366	10.64	17.45	23.95	35.17
6.1	181-114-225 - polyester	0	3,236	2,866	2,757	15.02	25.28	35.74	50.16
		90	3,087	2,739	2,598	11.83	22.52	30.61	46.82
1.11	182-114 - polyester	0	3,413	2,890	2,750	10.05	20.39	29.31	51.20
		90	3,461	2,897	2,728	9.00	18.02	25.94	51.72
1.2	128-114 - phenolic	0	2,782	2,454	2,345	10.74	20.30	28.59	37.48
		90	2,218	1,902	1,766	6.85	12.79	17.21	27.63
1.4	143-114 - phenolic	0	4,601	4,469	.....	38.52	71.50	.....	79.60
		90	1,701	1,256	1,026	3.50	4.75	5.23	9.56
1.6	164-114 - phenolic	0	2,005	1,765	1,636	8.17	14.81	17.19	19.96
		90	2,143	1,852	1,706	7.21	13.11	15.80	21.29
1.8	181-114-225 - phenolic	0	3,427	2,990	2,845	12.58	23.74	31.86	52.26
		90	3,394	3,038	2,729	12.31	21.19	29.30	49.44
1.10	181-114-225 - phenolic	0	3,582	3,132	2,976	12.91	23.24	31.79	51.37
		90	3,425	2,903	2,715	10.39	18.43	24.84	48.65
1.12	182-114 - phenolic	0	3,227	2,788	2,658	10.49	20.92	28.23	43.64
		90	3,288	2,762	2,598	9.09	18.28	25.45	47.38

### Series 2 -- Variations in Yarns

1.7 & 6.1	181-114-225 - polyester	0	3,275	2,901	2,769	13.09	23.81	33.35	45.70
		90	3,004	2,624	2,482	11.23	19.98	27.28	41.49
2.1	181-114-150 - polyester	0	3,390	2,890	2,757	11.41	20.92	29.42	50.94
		90	3,192	2,699	2,564	10.69	19.63	27.53	50.28
1.8 & 1.10	181-114-225 - phenolic	0	3,504	3,061	2,910	12.74	23.49	31.82	51.81
		90	3,364	2,995	2,722	11.35	19.81	27.07	49.02
2.2	181-114-150 - phenolic	0	3,483	3,265	3,110	10.92	21.87	31.32	50.95
		90	3,761	3,140	2,951	9.48	20.57	28.48	47.35

### Series 3 -- Variations in Finish

1.7 & 6.1	181-114-225 - polyester	0	3,275	2,901	2,769	13.09	23.81	33.35	45.70
		90	3,004	2,624	2,482	11.23	19.98	27.28	41.49
3.1	181-136 - polyester	0	2,877	2,456	2,343	8.55	17.87	25.09	40.42
		90	2,532	2,171	2,053	8.52	15.61	20.09	38.49
1.8 & 1.10	181-114-225 - phenolic	0	3,504	3,061	2,910	12.74	23.49	31.82	51.81
		90	3,364	2,995	2,722	11.35	19.81	27.07	49.02
3.2	181-136 - phenolic	0	2,696	2,365	.....	11.06	25.69	.....	33.84
		90	2,276	2,105	.....	15.08	26.73	.....	30.10

Z H 90645 F

(Page 1 of 2)

# NAVORD Report 2569

Table 3.--Results of tensile tests of glass-fabric-base plastic laminates  
(Continued)

F.P.L. panel No.	Factors investigated	Relation	Modulus of elasticity			Stress at -			
		of loaded	direction:	Initial:	Secant at:	Proportional:	0.1 per-	0.2 per-	Maximum
		to warp	to warp	to warp	to warp	to warp	to warp	to warp	to warp
				0.1 per-	0.2 per-	limit	cent	cent	cent
				cent	cent	strain	strain	strain	strain
				offset	offset	offset	offset	offset	offset
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)
		Degrees	1,000	1,000	1,000	1,000	1,000	1,000	1,000
			P.S.I.	P.S.I.	P.S.I.	P.S.I.	P.S.I.	P.S.I.	P.S.I.

## GROUP 2 -- VARIATIONS IN FABRICATION PROCEDURE

### Series 4 -- Variation in Thickness

4.1	1/2 inch thick	0	3,721	3,226	3,037	13.51	24.02	33.11	51.88
		90	3,733	3,134	2,939	10.46	19.49	27.72	53.88
4.3	1/4 inch thick	0	3,619	3,133	3,015	12.25	25.37	35.43	41.50
		90	3,455	2,911	2,737	8.87	18.77	26.68	35.84
1.7 & 6.1	1/8 inch thick	0	3,275	2,901	2,769	13.09	23.81	33.35	45.70
		90	3,004	2,624	2,482	11.23	19.98	27.28	41.49
4.5	1/16 inch thick	0	3,959	3,294	3,133	11.68	20.84	30.62	45.77
		90	3,428	2,848	2,711	10.37	18.94	27.07	40.25

### Series 5 -- Variation in Molding Pressure and Resin Content

5.1	39.5 percent	0	2,581	2,336	2,226	14.37	24.75	32.81	45.02
		90	2,785	2,476	2,362	12.26	23.20	31.43	47.11
5.3	41.6 percent	0	2,821	2,475	2,410	11.70	21.56	28.01	31.39
		90	2,597	2,266	2,126	10.85	19.34	24.24	29.38
1.7 & 6.1	35.5 percent	0	3,275	2,901	2,769	13.09	23.81	33.35	45.70
		90	3,004	2,624	2,482	11.23	19.98	27.28	41.49
5.5	30.0 percent	0	3,538	3,100	2,935	12.55	25.10	34.78	41.55
		90	3,552	2,997	2,800	9.82	18.71	26.33	37.54
5.7	21.8 percent	0	3,846	3,320	3,141	11.44	24.19	34.64	53.86
		90	3,911	3,256	3,055	9.86	20.74	30.10	53.08

## GROUP 3 -- VARIATIONS IN EVALUATION CONDITIONS

### Series 6 -- Variation in Temperature at Time of Test

1.9	-65° F.	0	4,077	3,367	3,193	12.01	20.39	29.92	57.10
		90	4,048	3,703	3,557	9.46	15.43	21.88	48.60
6.3	-35° F.	0	4,371	3,528	3,286	9.41	17.44	26.46	54.00
		90	4,064	3,274	3,118	8.97	16.62	26.73	52.30
6.5	0° F.	0	4,595	3,742	3,489	11.95	26.68	39.13	60.84
		90	3,839	3,252	3,101	10.36	20.56	31.14	59.32
6.7	30° F.	0	3,864	3,254	3,115	11.90	22.39	36.17	46.86
		90	4,225	3,389	3,097	11.77	17.34	25.16	40.64
1.7 & 6.1	75° F.	0	3,275	2,901	2,769	13.09	23.81	33.35	45.70
		90	3,004	2,624	2,482	11.23	19.98	27.28	41.49
6.9	120° F.	0	2,763	2,521	2,432	14.15	28.22	36.57	40.86
		90	2,765	2,548	2,437	13.94	30.11	38.17	44.76
6.11	160° F.	0	2,753	2,526	.....	13.37	26.86	.....	27.34
		90	2,192	1,943	.....	8.41	16.73	.....	21.27
6.2	-65° F.	0	4,390	3,731	3,519	12.64	24.49	34.93	66.30
		90	4,313	3,626	3,373	12.45	22.48	30.64	59.80
6.4	-35° F.	0	4,379	3,711	3,486	12.94	22.78	32.18	65.50
		90	4,054	3,253	3,018	13.81	22.93	30.24	54.40
6.6	0° F.	0	3,912	3,394	3,222	13.30	24.63	38.16	59.74
		90	3,574	3,050	2,823	11.65	19.07	26.07	44.18
6.8	30° F.	0	4,183	3,612	3,443	13.98	25.65	38.42	59.98
		90	3,964	3,332	3,153	11.14	20.12	29.65	52.24
1.8 & 1.10	75° F.	0	3,504	3,061	2,910	12.74	23.49	31.82	51.81
		90	3,364	2,995	2,722	11.35	19.81	27.07	49.02
6.10	120° F.	0	3,704	3,195	3,068	11.30	24.26	34.80	47.78
		90	3,450	2,952	2,766	10.62	19.79	27.17	46.97
6.12	160° F.	0	3,223	2,938	.....	12.32	30.18	.....	45.48
		90	3,192	2,851	2,742	11.67	26.04	36.43	46.21

# NAVORD Report 2669

Table 4.--Edgewise compressive strength of glass-fabric-base plastic laminates

Factors investigated :		Molded with polyester resin			Molded with phenolic resin		
		F.P.L. :			F.P.L. :		
		Maximum strength			Maximum strength		
		panel :			panel :		
		No.	Lengthwise	Crosswise	No.	Lengthwise	Crosswise
(1)	(2)	(3)	(4)	(5)	(6)	(7)	
			1,000	1,000		1,000	1,000
			p.s.i.	p.s.i.		p.s.i.	p.s.i.

## GROUP 1 -- VARIATIONS IN FABRICS

### Series 1 -- Variations in Weaves

128-114	: 1.1	:	23,890	:	29,570	:	1.2	:	20,290	:	24,770
143-114	: 1.3	:	50,650	:	24,100	:	1.4	:	40,900	:	17,850
164-114	: 1.5	:	24,370	:	22,940	:	1.6	:	12,460	:	16,020
181-114-225	: 1.7	:	33,970	:	33,640	:	1.8	:	32,890	:	40,280
181-114-225	: 1.9	:	34,190	:	38,190	:	1.10	:	38,600	:	35,720
182-114	: 1.11	:	32,460	:	39,550	:	1.12	:	30,300	:	35,420

### Series 2 -- Variations in Yarns

181-114-225	: 1.7 &	:	:	:	1.8 &	:	:	:	:	:	:
	: 1.9	:	34,080	:	35,920	:	1.10	:	35,740	:	38,000
181-114-150	: 2.1	:	33,480	:	37,420	:	2.2	:	35,410	:	37,820

### Series 3 -- Variations in Finish

181-114-225	: 1.7 &	:	:	:	1.8 &	:	:	:	:	:	:
	: 1.9	:	34,080	:	35,920	:	1.10	:	35,740	:	38,000
181-136	: 3.1	:	35,630	:	34,580	:	3.2	:	20,100	:	16,440

## GROUP 2 -- VARIATIONS IN FABRICATION PROCEDURE

### Series 4 -- Variation in Thickness

64 ply - 1/2 inch	: 4.1	:	42,910	:	38,260	:	:	:	:	:	:
32 ply - 1/4 inch	: 4.3	:	39,870	:	39,540	:	:	:	:	:	:
16 ply - 1/8 inch	: 1.7 &	:	:	:	:	:	:	:	:	:	:
	: 1.9	:	34,080	:	35,920	:	:	:	:	:	:
8 ply - 1/16 inch	: 4.5	:	23,370	:	28,920	:	:	:	:	:	:

### Series 5 -- Variation in Molding Pressure and Resin Content

59.5 percent	: 5.1	:	33,160	:	32,500	:	:	:	:	:	:
41.6 percent	: 5.3	:	32,700	:	35,340	:	:	:	:	:	:
30.0 percent	: 5.5	:	29,930	:	37,540	:	:	:	:	:	:
33.5 percent	: 1.7 &	:	:	:	:	:	:	:	:	:	:
	: 1.9	:	34,080	:	35,920	:	:	:	:	:	:
21.8 percent	: 5.7	:	30,000	:	35,160	:	:	:	:	:	:

## GROUP 3 -- VARIATIONS IN EVALUATION CONDITIONS

### Series 6 -- Variation in Temperature at Time of Test

-65° F.	: 6.1	:	44,340	:	38,080	:	6.2	:	44,100	:	42,000
-30° F.	: 6.3	:	30,700	:	37,360	:	6.4	:	48,560	:	43,580
0° F.	: 6.5	:	40,420	:	38,440	:	6.6	:	38,680	:	33,340
30° F.	: 6.7	:	41,940	:	39,860	:	6.8	:	41,360	:	37,180
77° F.	: 1.7 &	:	:	:	:	:	1.8 &	:	:	:	:
	: 1.9	:	34,080	:	35,920	:	1.10	:	35,740	:	38,000
120° F.	: 6.9	:	30,060	:	29,000	:	6.10	:	37,560	:	36,840
160° F.	: 6.11	:	17,130	:	12,760	:	6.12	:	35,790	:	31,990



# NAVORD Report 2669

Table 5.--Results of flexural tests on glass-fabric-base plastic laminates

F.P.L. panel No.	Factors investigated	Relation of span to warp	Modulus of elasticity			Fiber stress at -			Modulus of rupture
			Initial: tangent:	Secant to: 0.1 per- cent strain offset	Secant to: 0.2 per- cent strain offset	Proportional limit	0.1 per- cent strain offset	0.2 per- cent strain offset	
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)
		Degree	1,000 p.s.i.	1,000 p.s.i.	1,000 p.s.i.	1,000 p.s.i.	1,000 p.s.i.	1,000 p.s.i.	1,000 p.s.i.

## GROUP 1 -- VARIATIONS IN FABRICS

### Series 1 -- Variations in weaves

1.1	128-114 - polyester	0	3,009	2,814	2,674	28.0	59.6	44.7	46.0
		90	2,710	2,510	2,378	20.2	31.3	37.9	42.8
1.3	143-114 - polyester	0	4,383	4,194	.....	80.0	106.4	.....	106.5
		90	1,724	1,484	1,351	9.0	12.4	14.2	18.4
1.5	164-114 - polyester	0	2,688	2,451	2,295	23.0	33.3	57.4	43.7
		90	2,405	2,253	2,107	17.4	27.0	31.4	40.0
1.7	181-114-225 - polyester	0	3,347	3,122	.....	35.2	55.2	.....	57.5
		90	3,364	3,082	.....	25.2	45.0	.....	52.9
1.9	181-114-225 - polyester	0	3,392	3,163	.....	26.8	53.0	.....	59.2
		90	3,301	3,018	2,874	26.2	44.4	52.9	54.1
1.11	182-114 - polyester	0	3,384	3,147	2,984	27.5	47.2	54.4	56.7
		90	3,355	3,119	2,939	25.0	46.9	52.0	59.6
1.2	128-114 - phenolic	0	2,646	2,472	.....	22.9	33.9	.....	34.8
		90	2,260	2,103	1,935	21.0	30.2	33.7	34.9
1.4	143-114 - phenolic	0	4,535	4,739	4,478	75.4	94.0	97.9	98.4
		90	1,717	1,472	1,353	7.8	11.2	13.4	18.7
1.6	164-114 - phenolic	0	2,837	1,869	1,706	17.6	21.6	23.4	24.3
		90	2,044	1,856	1,732	15.9	21.9	23.5	24.1
1.8	181-114-225 - phenolic	0	3,358	3,167	3,037	31.5	50.8	58.9	65.5
		90	3,221	3,334	3,169	34.1	51.4	58.8	59.8
1.10	181-114-225 - phenolic	0	3,583	3,376	3,258	31.4	53.0	67.3	69.7
		90	3,319	3,095	2,946	26.9	43.0	50.4	58.2
1.12	182-114 - phenolic	0	3,296	3,068	2,914	31.0	45.8	51.6	54.6
		90	3,065	2,868	2,717	30.3	46.1	49.1	49.9

### Series 2 -- Variations in Yarns

1.7 & 1.9	181-114-225 - polyester	0	3,369	3,142	.....	31.0	54.1	.....	58.3
		90	3,332	3,050	.....	25.7	44.7	.....	53.5
2.1	181-114-150 - polyester	0	3,416	3,207	3,034	29.8	54.1	60.4	60.8
		90	3,332	3,119	2,974	31.5	48.1	57.7	61.4
1.8 & 1.10	181-114-225 - phenolic	0	3,470	3,271	3,147	31.4	51.9	63.1	67.6
		90	3,420	3,215	3,057	30.5	47.2	54.6	58.5
2.2	181-114-150 - phenolic	0	3,787	3,544	3,370	32.6	52.1	61.3	63.9
		90	3,571	3,373	3,205	30.9	50.8	58.0	59.1

### Series 3 -- Variations in Finish

1.7 & 1.9	181-114-225 - polyester	0	3,369	3,142	.....	31.0	54.1	.....	58.3
		90	3,332	3,050	.....	25.7	44.7	.....	53.5
3.1	181-136 - polyester	0	2,555	2,423	.....	30.7	55.2	.....	59.5
		90	2,280	2,155	.....	33.3	46.0	.....	50.9
1.8 & 1.10	181-114-225 - phenolic	0	3,470	3,271	3,147	31.4	51.9	63.1	67.6
		90	3,420	3,215	3,057	30.5	47.2	54.6	58.5
3.2	181-136 - phenolic	0	2,550	2,330	.....	27.9	34.1	.....	34.8
		90	2,173	2,026	1,954	18.8	26.1	29.0	31.3

Z M 90648 F

(Page 1 of 2)

# NAVORD Report 2669

Table 5.--Results of flexural tests on glass-fabric base plastic laminates (Continued)

F.P.I. panel No.	Factors investigated	Relation of span to direction of warp	Modulus of elasticity		Fiber stress at		Modulus of rupture	
			Initial tangent	Secant 0.1 per- cent strain offset	Proportional limit 0.2 per- cent strain offset	0.1 per- cent offset	0.2 per- cent offset	
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)
		Degrees	1,000 p.s.i.	1,000 p.s.i.	1,000 p.s.i.	1,000 p.s.i.	1,000 p.s.i.	1,000 p.s.i.

## GROUP 2 -- VARIATIONS IN FABRICATION PROCEDURE

### Series 4 -- Variation in Thickness

4.1	1/2 inch	0	3,892	3,623	26.8	53.3	56.2
		90	3,782	3,504	22.2	47.2	51.9
4.3	1/4 inch	0	3,969	3,719	24.9	56.7	61.0
		90	3,825	3,563	20.7	47.8	55.5
1.7 & 1.9	1/8 inch	0	3,369	3,142	31.0	54.1	58.3
		90	3,332	3,050	25.7	44.7	53.5
4.5	1/16 inch	0	3,707	3,491	32.3	56.6	62.2
		90	4,002	3,693	24.4	43.8	53.0

### Series 5 -- Variation in Molding Pressure and Resin Content

5.1	39.5 percent	0	2,836	2,761	2,654	30.8	47.6	54.5	57.2
		90	2,838	2,755	2,635	28.9	45.6	51.2	58.5
5.3	41.6 percent	0	3,189	3,017	2,708	26.3	45.1	50.8	
		90	3,017	2,832	2,708	25.7	41.3	48.7	49.4
1.7 & 1.9	33.5 percent	0	3,369	3,142		31.0	54.1	58.3	
		90	3,332	3,050		25.7	44.7	53.6	
5.5	30.0 percent	0	3,985	3,756	3,596	27.4	47.1	59.8	63.1
		90	3,610	3,379	3,221	26.1	46.6	52.6	54.1
5.7	21.8 percent	0	4,137	3,797	3,585	22.4	45.4	53.7	54.8
		90	3,879	3,587		25.9	48.9	51.6	

## GROUP 3 -- VARIATIONS IN EVALUATION CONDITIONS

### Series 6 -- Variation in Temperature at Time of Test

6.1	-65° F.	0	3,562	3,370	3,218	52.4	67.0	73.2	73.8
		90	3,521	3,313		6.0	68.6		72.0
6.3	-30° F.	0	3,608	3,433		45.3	67.8		70.4
		90	3,334	3,188		49.3	73.6		77.4
6.5	0° F.	0	3,800	3,608		48.9	66.2		71.2
		90	3,513	3,313		44.6	61.8		66.6
6.7	30° F.	0	3,639	3,620	3,434	42.7	59.6	64.2	64.9
		90	3,532	3,322	3,160	35.7	55.0	61.8	63.3
1.7 & 1.9	75° F.	0	3,369	3,142		31.0	54.1		58.3
		90	3,332	3,050		25.7	44.7		53.6
6.9	120° F.	0	3,031	2,798	2,648	19.7	33.9	41.9	45.1
		90	2,959	2,674	2,529	20.3	31.2	39.3	43.1
6.11	160° F.	0	2,278	2,011	1,863	10.8	18.8	22.4	24.2
		90	1,888	1,709	1,591	9.9	16.7	20.4	24.2
6.2	-65° F.	0	3,619	3,467		60.2	80.3		85.1
		90	3,478	3,294		44.4	62.4		66.9
6.4	-30° F.	0	3,810	3,642		59.3	78.9		82.0
		90	3,478	3,326	3,202	42.2	64.4	57.3	74.7
6.6	0° F.	0	3,626	3,466		44.5	68.1		76.8
		90	3,514	3,275	3,163	33.6	52.2	63.1	69.3
5.8	30° F.	0	4,363	4,051	3,878	37.7	62.5	74.0	78.4
		90	3,330	3,273	3,128	29.4	47.1	56.5	67.2
1.8 & 1.10	75° F.	0	3,470	3,271	3,147	31.4	51.9	63.1	67.6
		90	3,420	3,215	3,057	30.5	47.2	54.6	58.5
6.10	120° F.	0	3,713	3,475	3,335	29.7	47.9	61.0	66.7
		90	3,606	3,364	3,216	27.4	43.8	53.9	58.5
6.12	160° F.	0	3,360	3,156	3,012	28.6	48.0	55.3	57.1
		90	3,217	2,974	2,840	26.8	39.3	46.8	52.4

# NAVORD Report 2669

Table 6.--Flatwise shear strength of glass-fabric-base laminates  
(Johnson-type shear)

Factors Investigated	Molded with polyester resin			Molded with phenolic resin		
	F.P.L. : panel No.	Flatwise strength		F.P.L. : panel No.	Flatwise strength	
		Lengthwise	Crosswise		Lengthwise	Crosswise
(1)	(2)	(3)	(4)	(5)	(6)	(7)
		1,000 P.S.I.	1,000 P.S.I.		1,000 P.S.I.	1,000 P.S.I.
GROUP 1 -- VARIATIONS IN FABRICS						
Series 1 -- Variations in Weaves						
128-114	1.1	19.98	21.78	1.2	10.11	9.26
143-114	1.3	10.21	27.15	1.4	6.89	21.09
164-114	1.5	19.51	20.15	1.6	7.22	7.21
181-114-225	1.7	20.30	21.88	1.8	15.00	17.26
181-114-225	1.9	20.07	21.01	1.10	16.46	18.12
182-114	1.11	22.37	21.24	1.12	12.53	12.51
Series 2 -- Variations in Yarns						
181-114-225	1.7 &			1.8 &		
	1.9	20.18	21.44	1.10	15.73	17.69
181-114-150	2.1	22.22	21.94	2.2	14.89	15.99
Series 3 -- Variations in Finish						
181-114-225	1.7 &			1.8 &		
	1.9	20.18	21.44	1.0	15.73	17.69
181-136	3.1	16.68	17.62	3.2	11.64	11.98
GROUP 2 -- VARIATIONS IN FABRICATION PROCEDURE						
Series 4 -- Variation in Thickness						
64 ply - 1/2 inch	4.1	21.90	23.72			
32 ply - 1/4 inch	4.3	20.49	22.60			
16 ply - 1/8 inch	1.7 &					
	1.9	20.18	21.44			
8 ply - 1/16 inch	4.5	21.25	23.19			
Series 5 -- Variation in Molding Pressure and Resin Content						
39.5 percent	5.1	19.15	19.02			
41.6 percent	5.3	18.21	19.78			
30.0 percent	5.5	21.46	23.13			
33.5 percent	1.7 &	20.18	21.44			
	1.9					
21.8 percent	5.7	21.27	21.22			
GROUP 3 -- VARIATIONS IN EVALUATION CONDITIONS						
Series 6 -- Variation in Temperature at Time of Test						
-65° F.	6.1	30.04	30.20	6.2	20.55	24.94
-30° F.	6.3	27.28	28.05	6.4	19.85	22.59
0° F.	6.5	27.80	25.95	6.6	19.01	23.21
30° F.	6.7	22.93	25.90	6.8	17.81	18.03
77° F.	1.7 &			1.8 &		
	1.9	20.18	21.44	1.10	15.73	17.69
120° F.	6.9	17.63	18.43	6.10	15.67	17.03
160° F.	6.11	14.41	15.45	6.12	13.43	15.74

# NAVORD Report 2669

Table 7.--Edgewise Izod impact strength of glass-fabric laminates

Factors investigated	Molded with polyester resin			Molded with phenolic resin		
	F.P.L. : Edgewise notch			F.P.L. : Edgewise notch		
	panel			panel		
	No.	Lengthwise	Crosswise	No.	Lengthwise	Crosswise
(1)	(2)	(3)	(4)	(5)	(6)	(7)
		<u>Ft.-lb. per</u> <u>in. of</u> <u>width</u>	<u>Ft.-lb. per</u> <u>in. of</u> <u>width</u>		<u>Ft.-lb. per</u> <u>in. of</u> <u>width</u>	<u>Ft.-lb. per</u> <u>in. of</u> <u>width</u>

## GROUP 1 -- VARIATIONS IN MATERIALS

### Series 1 -- Variations in Weaves

128-114	: 2.1	: 20.4	: 15.9	: 1.2	: 12.9	: 10.0
143-114	: 1.3	: 36.1	: 2.3	: 1.4	: 43.9	: 2.4
164-114	: 1.3	: 23.8	: 20.1	: 1.6	: 11.3	: 11.0
181-114-225	: 1.7	: 12.7	: 10.5	: 1.8	: 21.0	: 18.1
181-114-225	: 1.9	: 11.0	: 9.8	: 1.10	: 19.9	: 16.5
182-114	: 1.11	: 20.6	: 21.0	: 1.12	: 20.9	: 20.9

### Series 2 -- Variations in Yarns

181-114-150	: 2.1	: 19.0	: 18.5	: 2.2	: 19.5	: 16.9
181-114-225	: 1.7 &	:	:	: 1.8 &	:	:
	: 1.9	: 11.8	: 10.2	: 1.10	: 20.4	: 17.3

### Series 3 -- Variations in Finish

181-136	: 3.1	: 13.9	: 12.0	: 3.2	: 10.1	: 7.2
181-114-225	: 1.7 &	:	:	: 1.8 &	:	:
	: 1.9	: 11.8	: 10.2	: 1.10	: 20.4	: 17.3

## GROUP 2 -- VARIATIONS IN FABRICATION PROCEDURE

### Series 4 -- Variation in Thickness

64 ply - 1/2 inch	: 4.1	: 18.1	: 17.0	:	:	:
32 ply - 1/4 inch	: 4.3	: 11.8	: 10.0	:	:	:
16 ply - 1/8 inch	: 1.7 &	:	:	:	:	:
	: 1.9	: 11.8	: 10.2	:	:	:
8 ply - 1/16 inch	: 4.5	: 13.9	: 12.3	:	:	:

### Series 5 -- Variation in Molding Pressure and Resin Content

39.5 percent	: 5.1	: 17.3	: 15.3	:	:	:
41.6 percent	: 5.3	: 8.6	: 7.0	:	:	:
50.0 percent	: 5.5	: 11.2	: 9.5	:	:	:
55.5 percent	: 1.7 &	:	:	:	:	:
	: 1.9	: 11.8	: 10.2	:	:	:
21.8 percent	: 5.7	: 23.4	: 22.1	:	:	:

## GROUP 3 -- VARIATIONS IN EVALUATION CONDITIONS

### Series 6 -- Variation in Temperature at Time of Test

-65° F.	: 6.1	: 26.4	: 24.7	: 6.2	: 28.8	: 25.8
-30° F.	: 6.3	: 18.5	: 16.8	: 6.4	: 28.0	: 22.2
0° F.	: 6.5	: 23.5	: 22.5	: 6.6	: 26.8	: 22.0
30° F.	: 6.7	: 13.7	: 10.8	: 6.8	: 24.1	: 20.5
77° F.	: 1.7 &	:	:	: 1.8 &	:	:
	: 1.9	: 11.8	: 10.2	: 1.10	: 20.4	: 17.3
120° F.	: 6.9	: 17.7	: 16.8	: 6.10	: 18.5	: 16.7
160° F.	: 6.11	: 10.8	: 8.8	: 6.12	: 16.1	: 16.0

Table 8. -- Dielectric constant and power factor of glass-cloth laminates

P.F.L. panel No.	Factor: investigated	Resin content	Specific gravity	Dielectric constant	Power factor
Percent					

## GROUP 1 -- VARIATIONS IN FABRICS

Series 1 -- Variations in Weaves

1.1	128-114 - polyester	38.1	1.815	4.03	0.0100
1.3	143-114 - polyester	37.2	1.805	4.04	0.0119
1.5	164-114 - polyester	38.1	1.805	4.16	0.0116
1.7	181-114-225 - polyester	33.4	1.892	4.42	0.0102
1.9	181-114-225 - polyester	33.7	1.878	4.32	0.0113
1.11	182-114 - polyester	32.7	1.910	4.47	0.0106
1.2	128-114 - phenolic	29.3	1.785	3.79	0.0266
1.4	143-114 - phenolic	24.5	1.733	4.30	0.0288
1.6	164-114 - phenolic	24.8	1.740	3.60	0.0237
1.8	181-114-225 - phenolic	23.2	1.815	4.55	0.0248
1.10	181-114-225 - phenolic	24.5	1.848	4.71	0.0246
1.12	182-114 - phenolic	22.7	1.726	4.35	0.0237

Series 2 -- Variations in Yarns

2.1	181-114-150 - polyester	33.1	1.893	4.42	0.0086
2.2	181-114-150 - phenolic	22.3	1.831	4.48	0.0230

Series 3 -- Variations in Finish

3.1	181-136 - polyester	44.7	1.758	4.05	0.0095
3.2	181-136 - phenolic	36.5	1.685	4.56	0.0415

## GROUP 2 -- VARIATIONS IN FABRICATION PROCEDURE

Series 4 -- Variation in Thickness

4.1	1/2 inch - polyester	27.0	1.975	4.67	0.0084
4.3	1/4 inch - polyester	28.3	1.957	4.56	0.0045
4.5	1/16 inch - polyester	27.9	1.987	4.61	0.0097

Series 5 -- Variation in Molding Pressure and Resin Content

5.1	2 p.s.i. - polyester	39.5	1.796	4.16	0.0101
5.3	10 p.s.i. - polyester	41.6	1.786	4.12	0.0107

Table 8. -- Dielectric constant and power factor of glass-cloth laminates  
(Continued)

F.P.L. panel No.	Factors investigated	Resin content	Specific gravity	Dielectric constant	Power factor
------------------------	----------------------	------------------	---------------------	------------------------	-----------------

: Percent :

5.5 : 45 p.s.i. - polyester : 30.0 : 1.936 : 4.72 : .0117  
5.7 : 395 p.s.i. - polyester : 21.8 : 2.038 : 4.74 : .0098

GROUP 3 -- VARIATIONS IN EVALUATION  
CONDITIONS

Series 6 -- Variation in Temperature at Time of Test<sup>2</sup>

6.1	: Polyester	: 32.1	: 1.916	: 4.43	: 0.0109
6.3	: do.	: 33.3	: 1.880	: 4.39	: .0109
6.5	: do.	: 30.0	: 1.908	: 4.48	: .0096
6.7	: do.	: 31.5	: 1.912	: 4.36	: .0104
6.9	: do.	: 36.4	: 1.878	: 4.44	: .0103
6.11	: do.	: 32.1	: 1.912	: 4.41	: .0100
6.2	: Phenolic	: 23.6	: 1.822	: 4.47	: .0249
6.4	: do.	: 23.6	: 1.855	: 4.51	: .0247
6.6	: do.	: 23.5	: 1.859	: 4.63	: .0240
6.8	: do.	: 23.8	: 1.840	: 4.65	: .0248
6.10	: do.	: 23.3	: 1.857	: 4.58	: .0228
6.12	: do.	: 23.9	: 1.840	: 4.57	: .0232

<sup>1</sup> Abnormally low specific gravity.

<sup>2</sup> Electrical tests were made at room temperature.

Fig. 1. Properties of Plastic Laminates Made of Different Fabrics & Resins

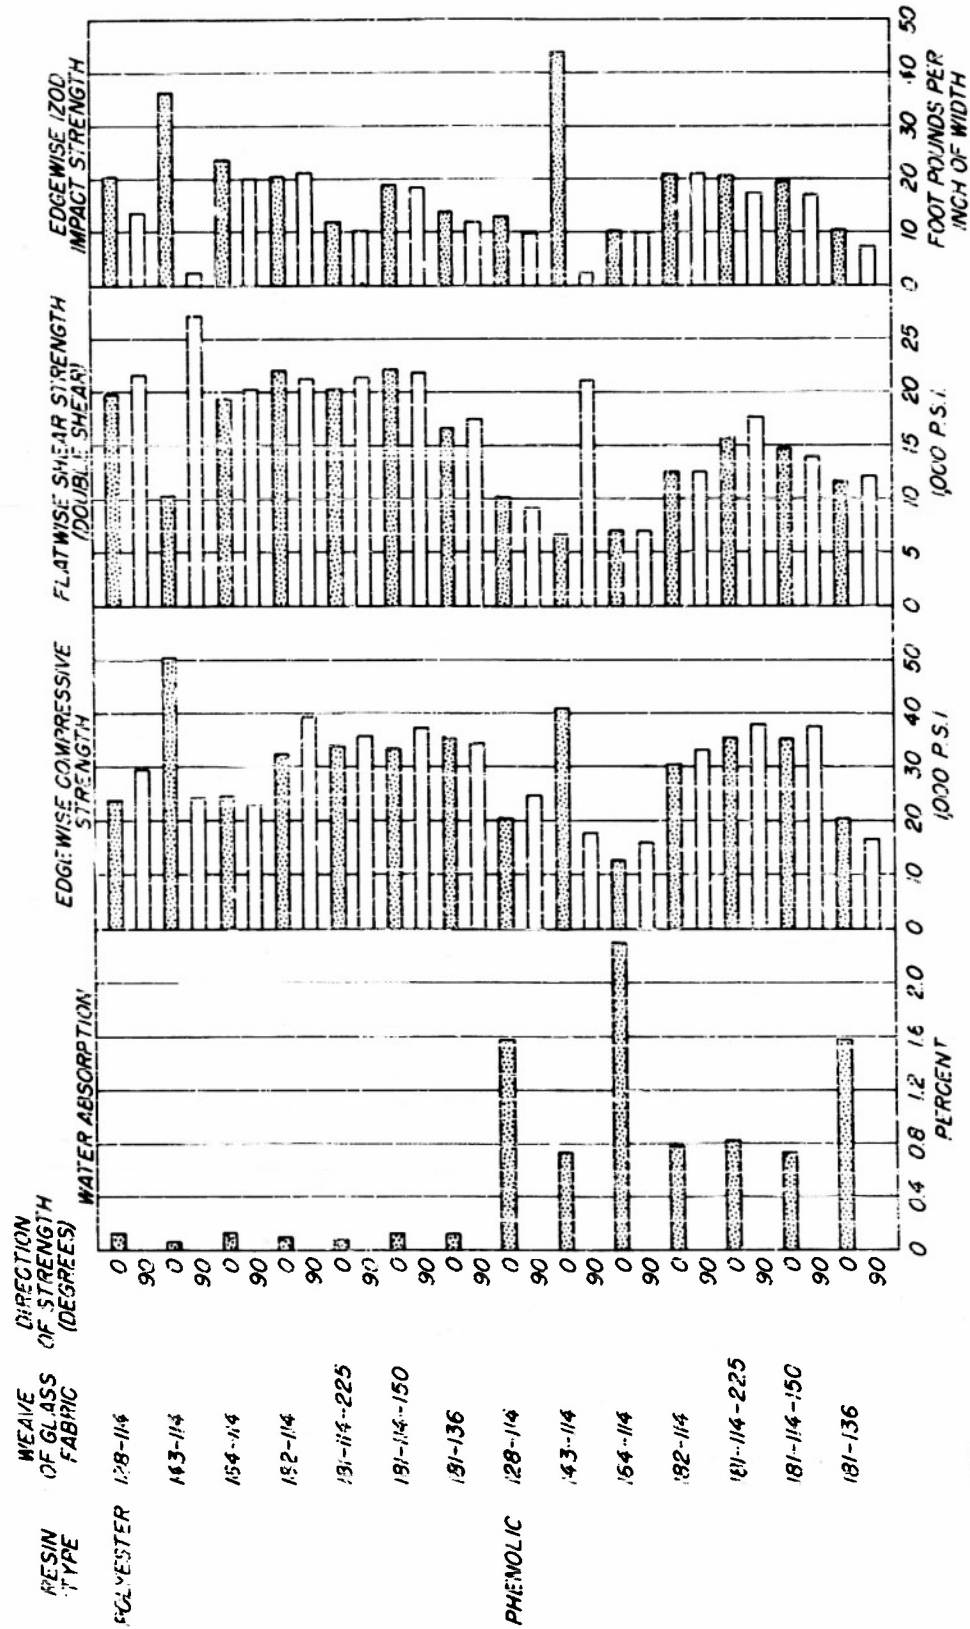
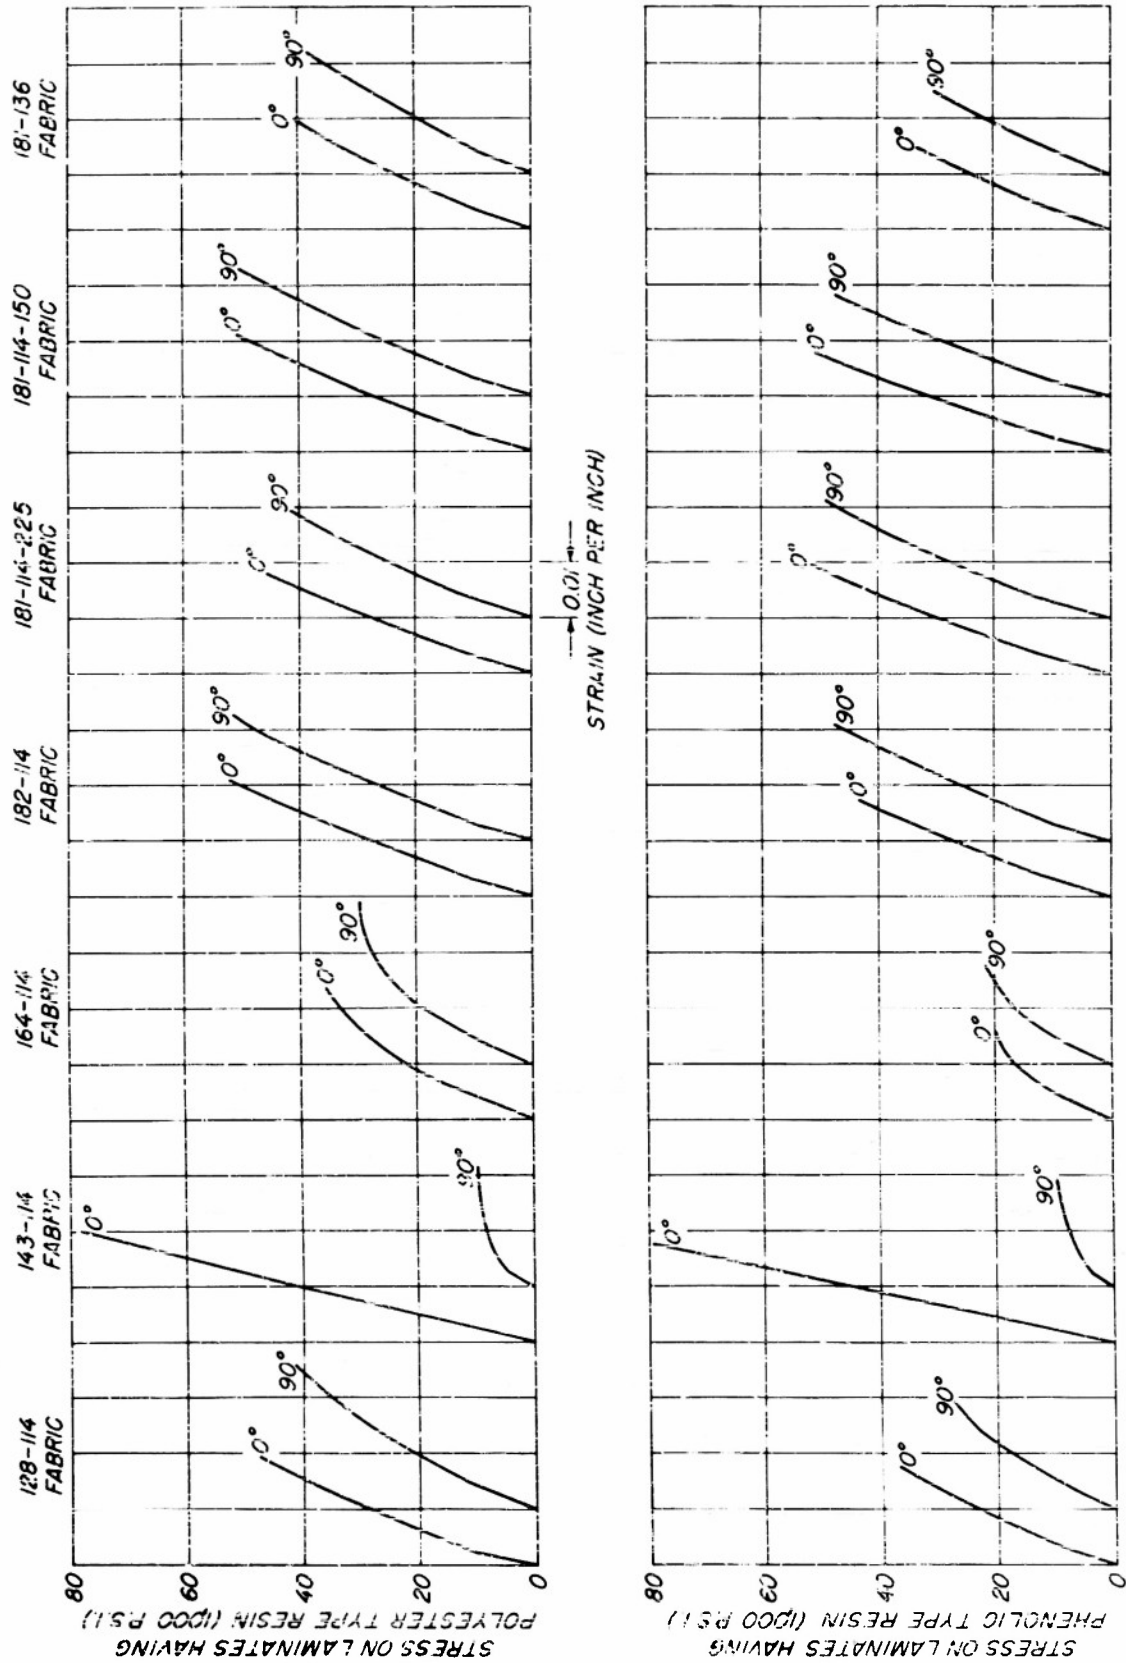


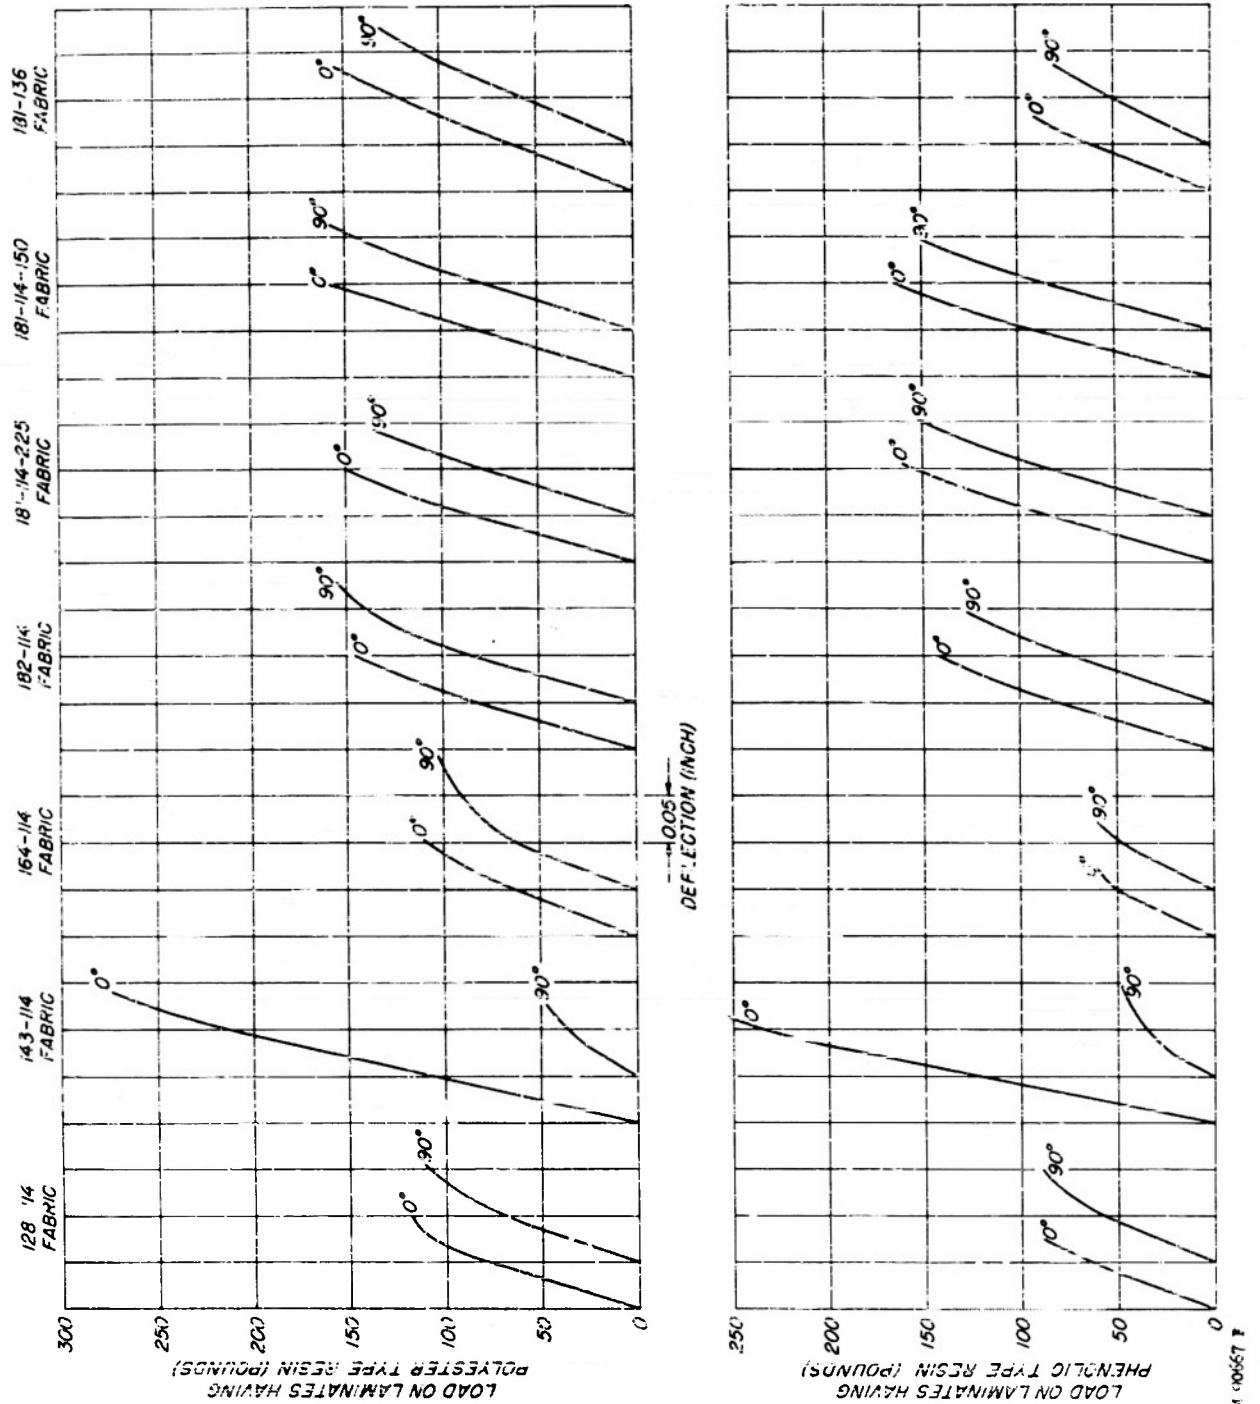


Fig. 2 Tensile Stress-Strain Curves of Plastic Laminates Made of Different Fabrics and Resins



# NAVCOR REPORT 2669

Fig. 3. Load-Deformation Curve in Flexure For Plastic Laminates Made of Different Fabrics and Resins



# NAVORD REPORT 2669

Fig. 4 Effect of Laminating Conditions on the Compressive, Shear, and Izod Impact Strength of Plastic Laminates

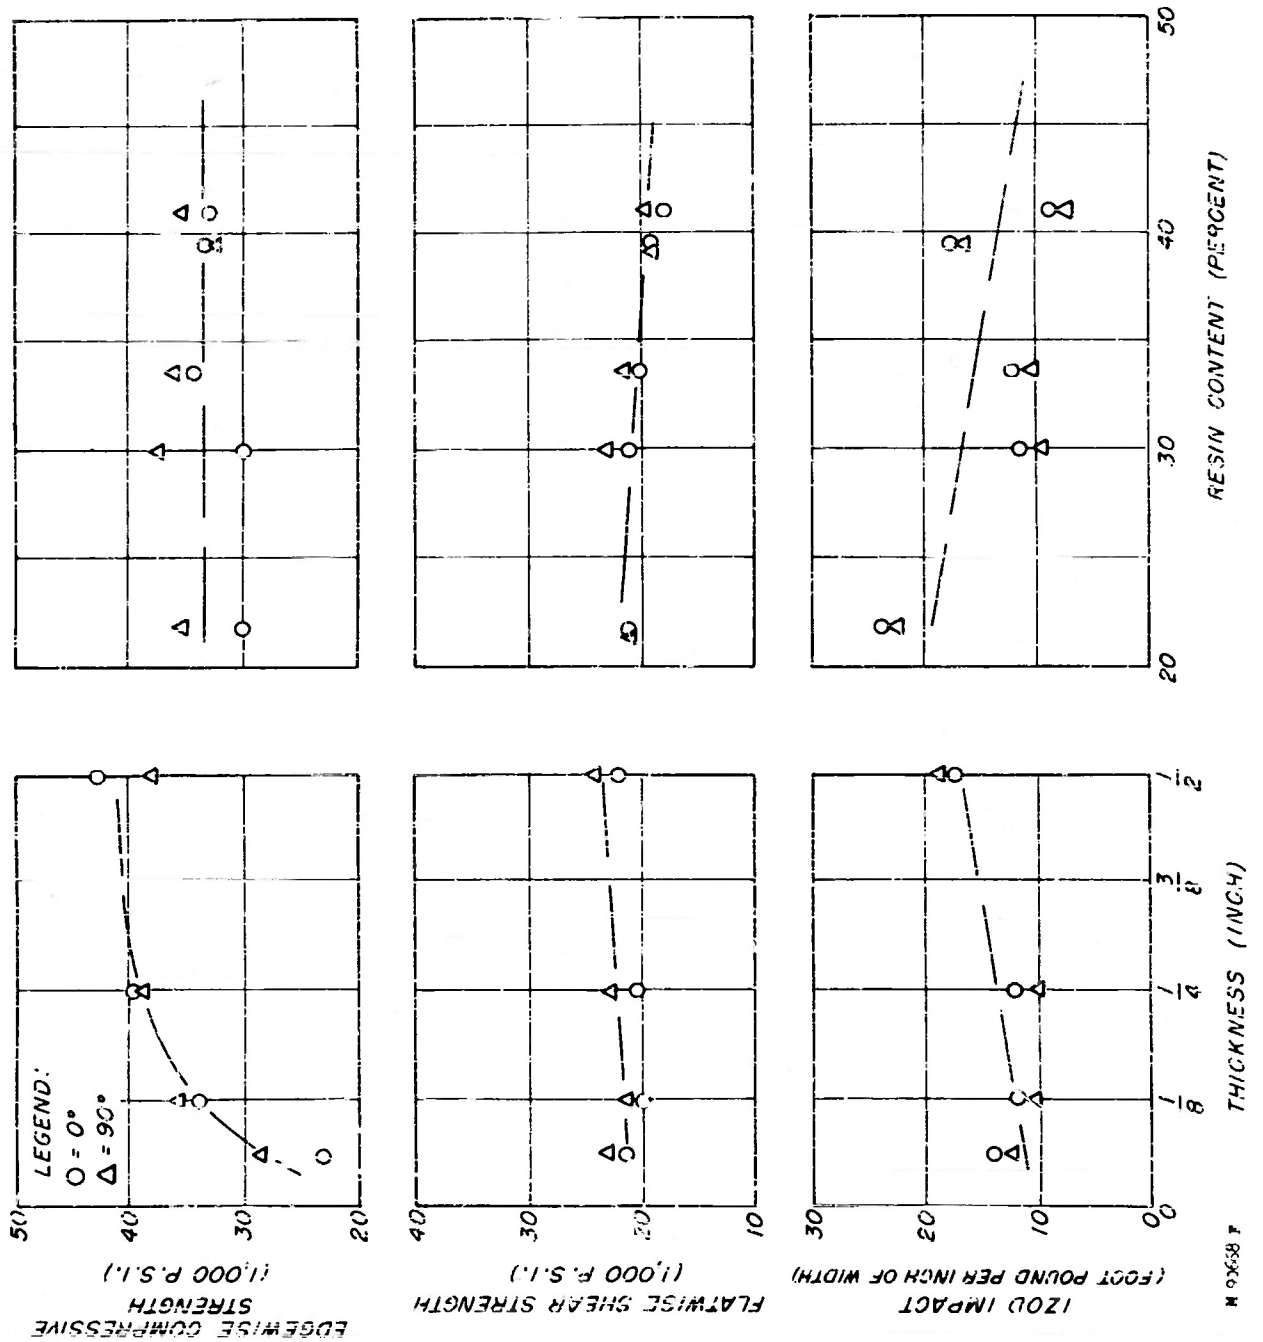


Fig. 5 Effect of Laminating Conditions on Tensile Properties of Plastic Laminates

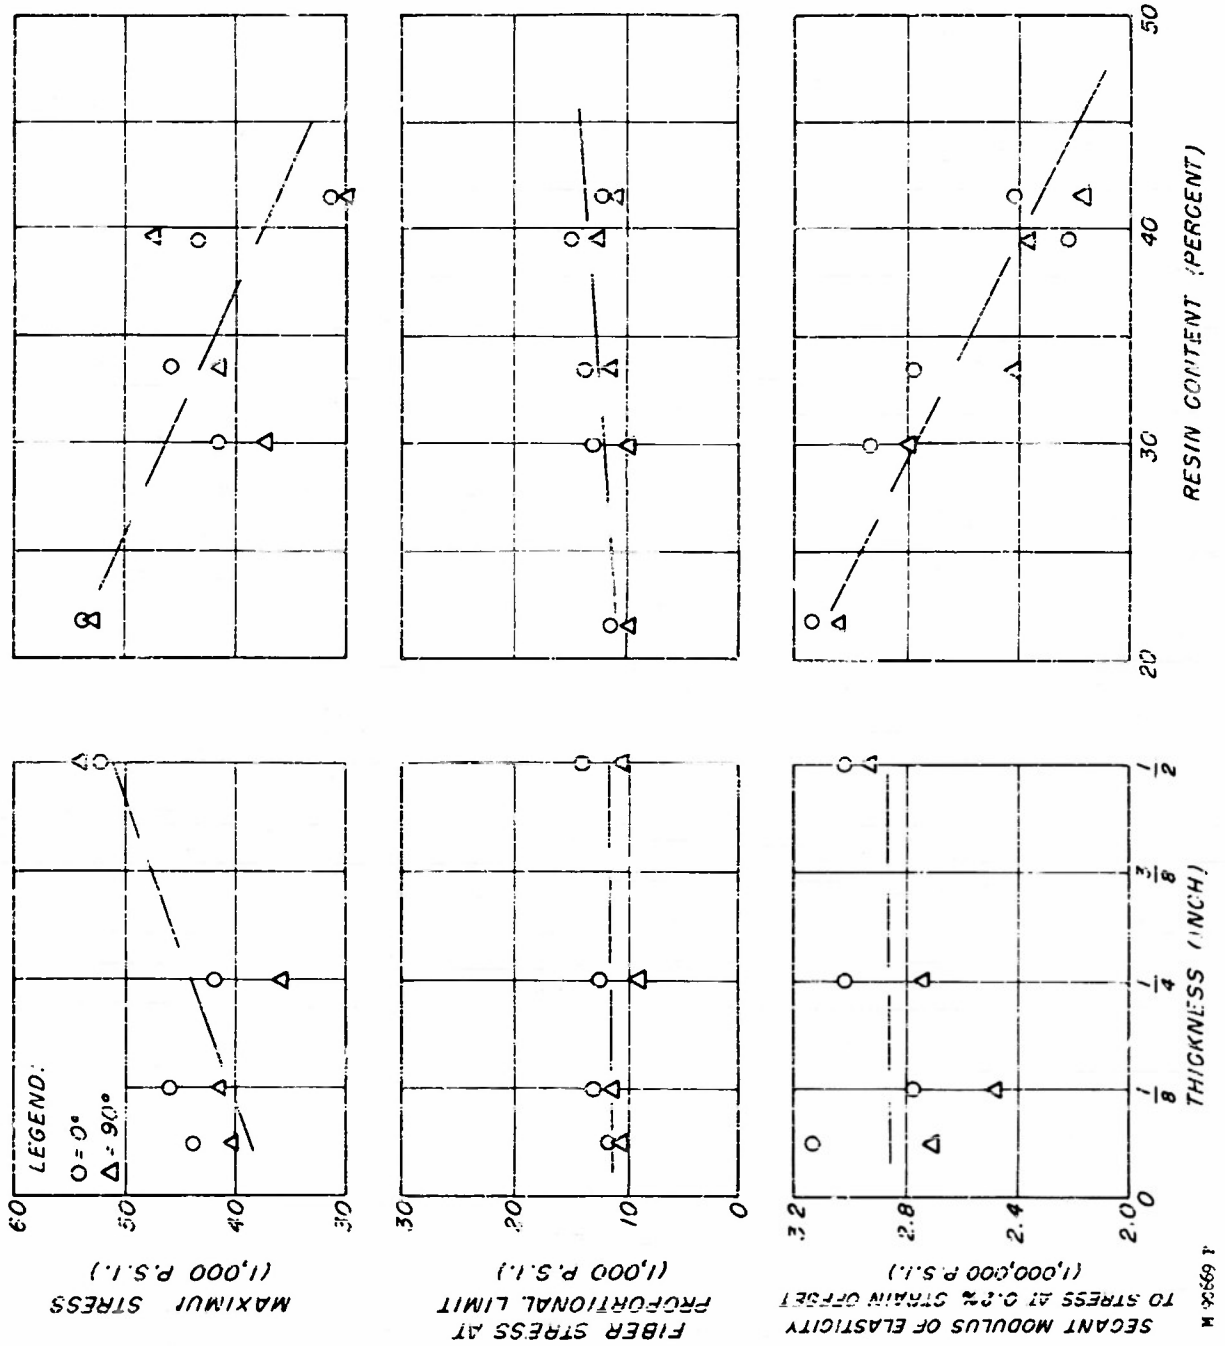
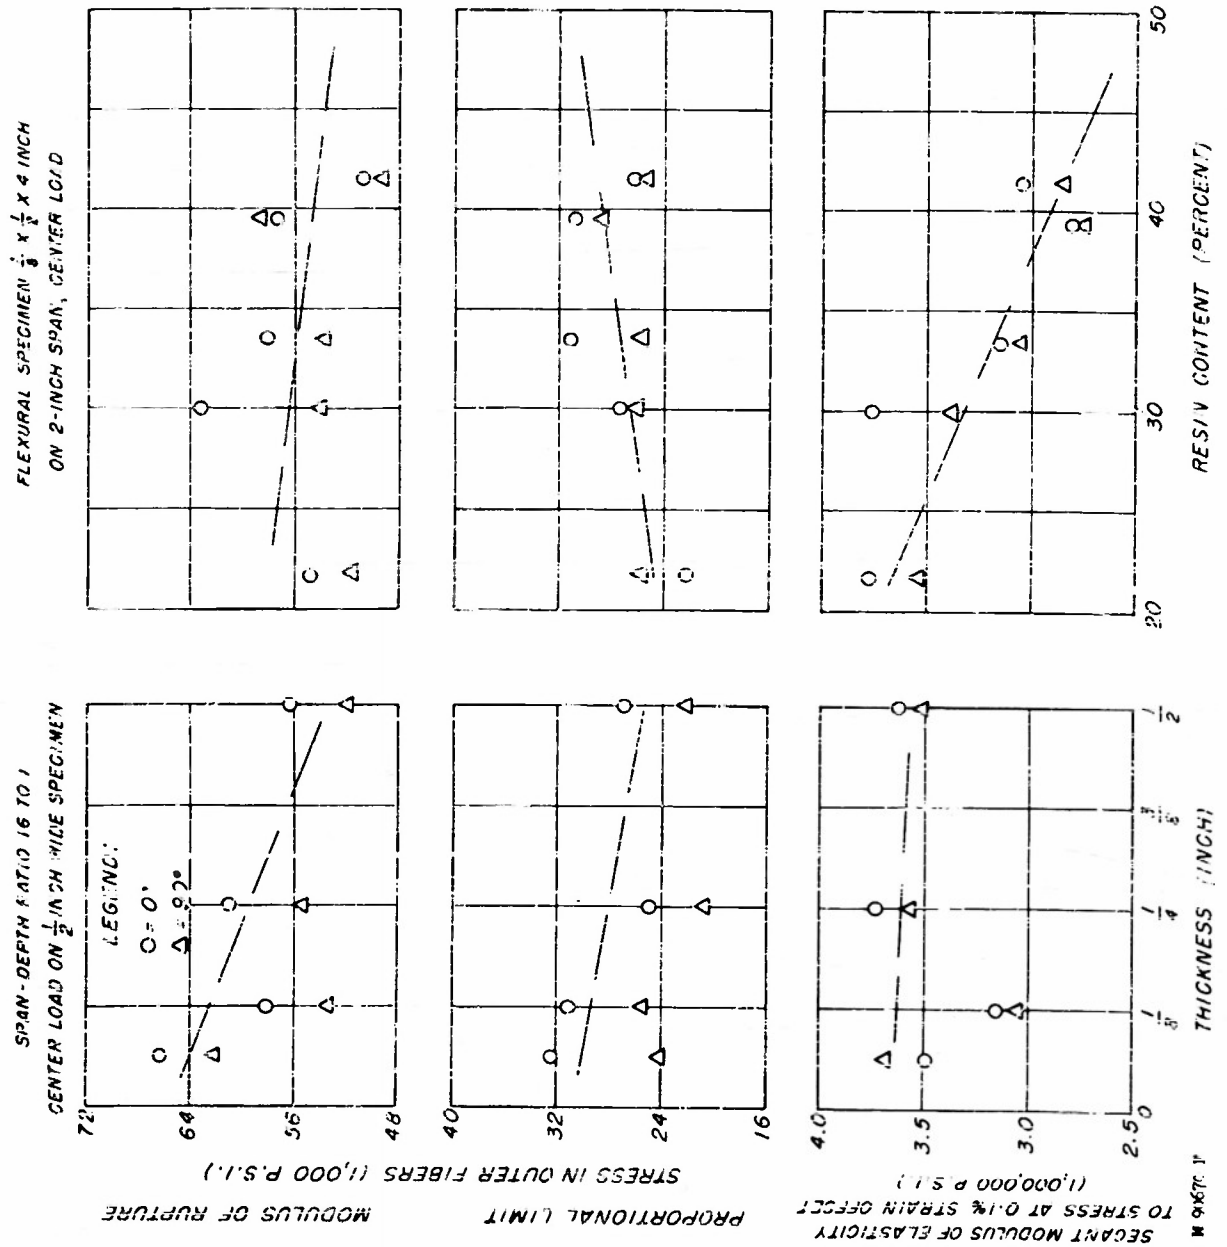


Fig. 6 Effect of Laminating Conditions on the Flexural Properties of Plastic Laminates



NAVORD REPORT 2669

Fig. 7 Effect of Temperature at Time of Test on Compressive, Shear, and Izod Impact Strength of Plastic Laminates

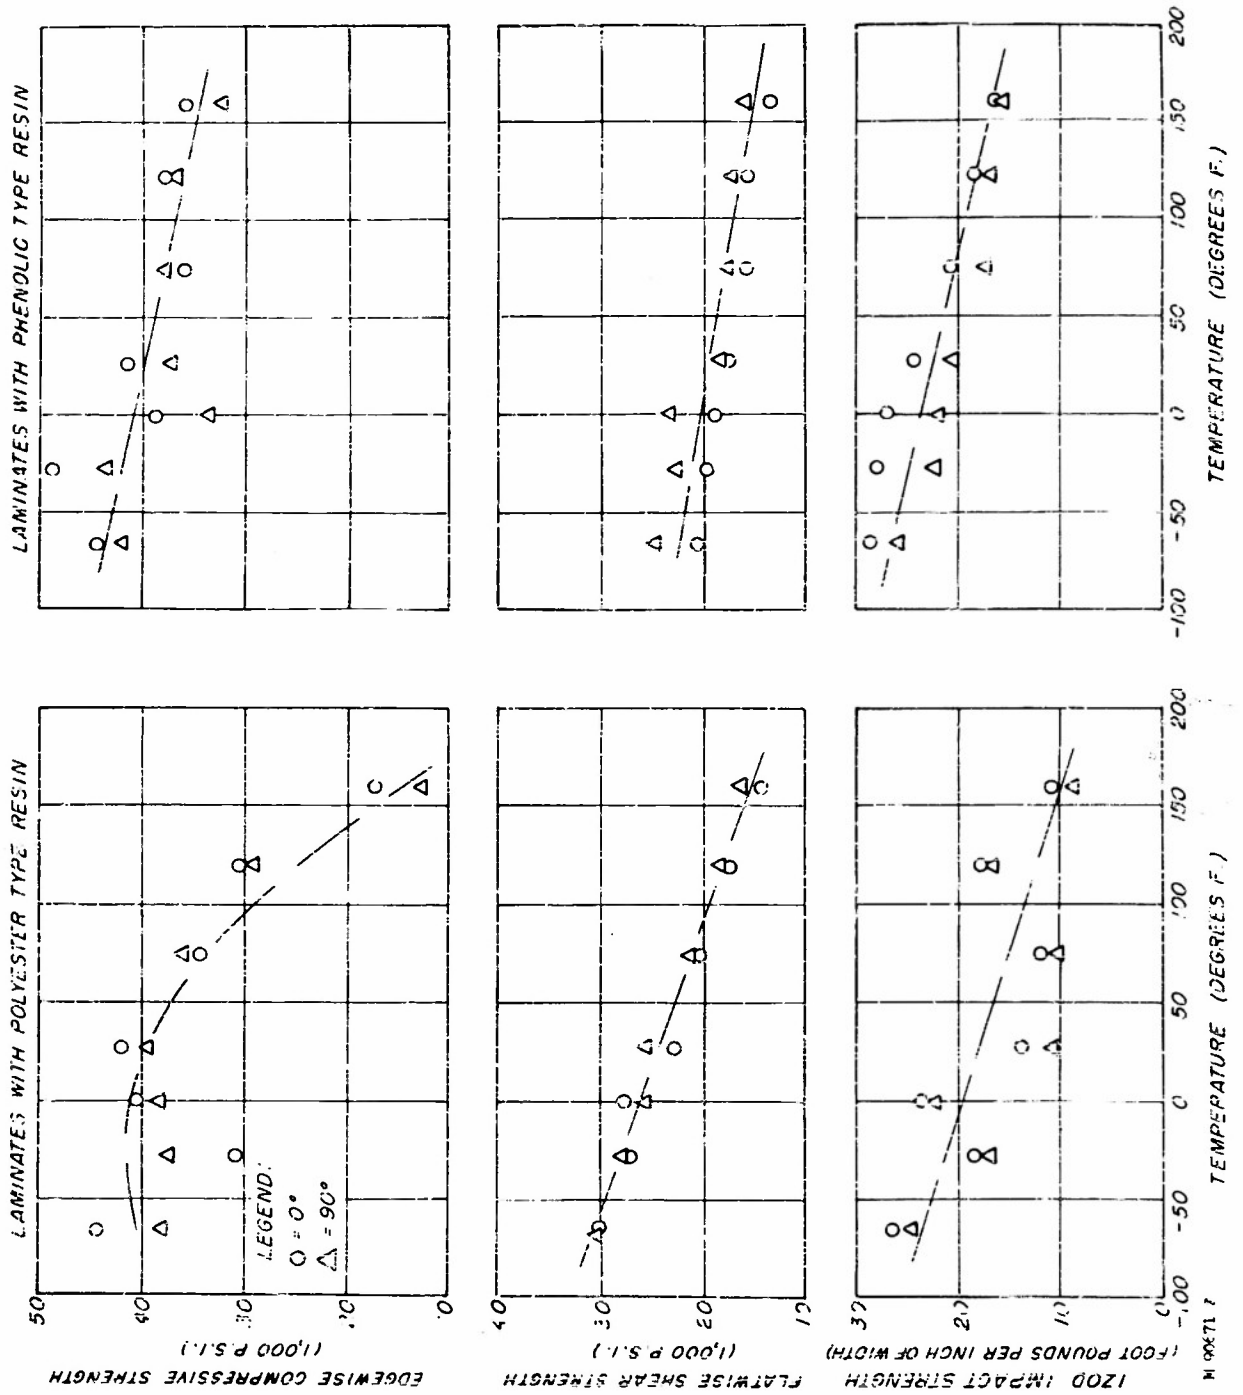


Fig. 3 Effect of Temperature at Time of Test on Tensile Properties of Plastic Laminates

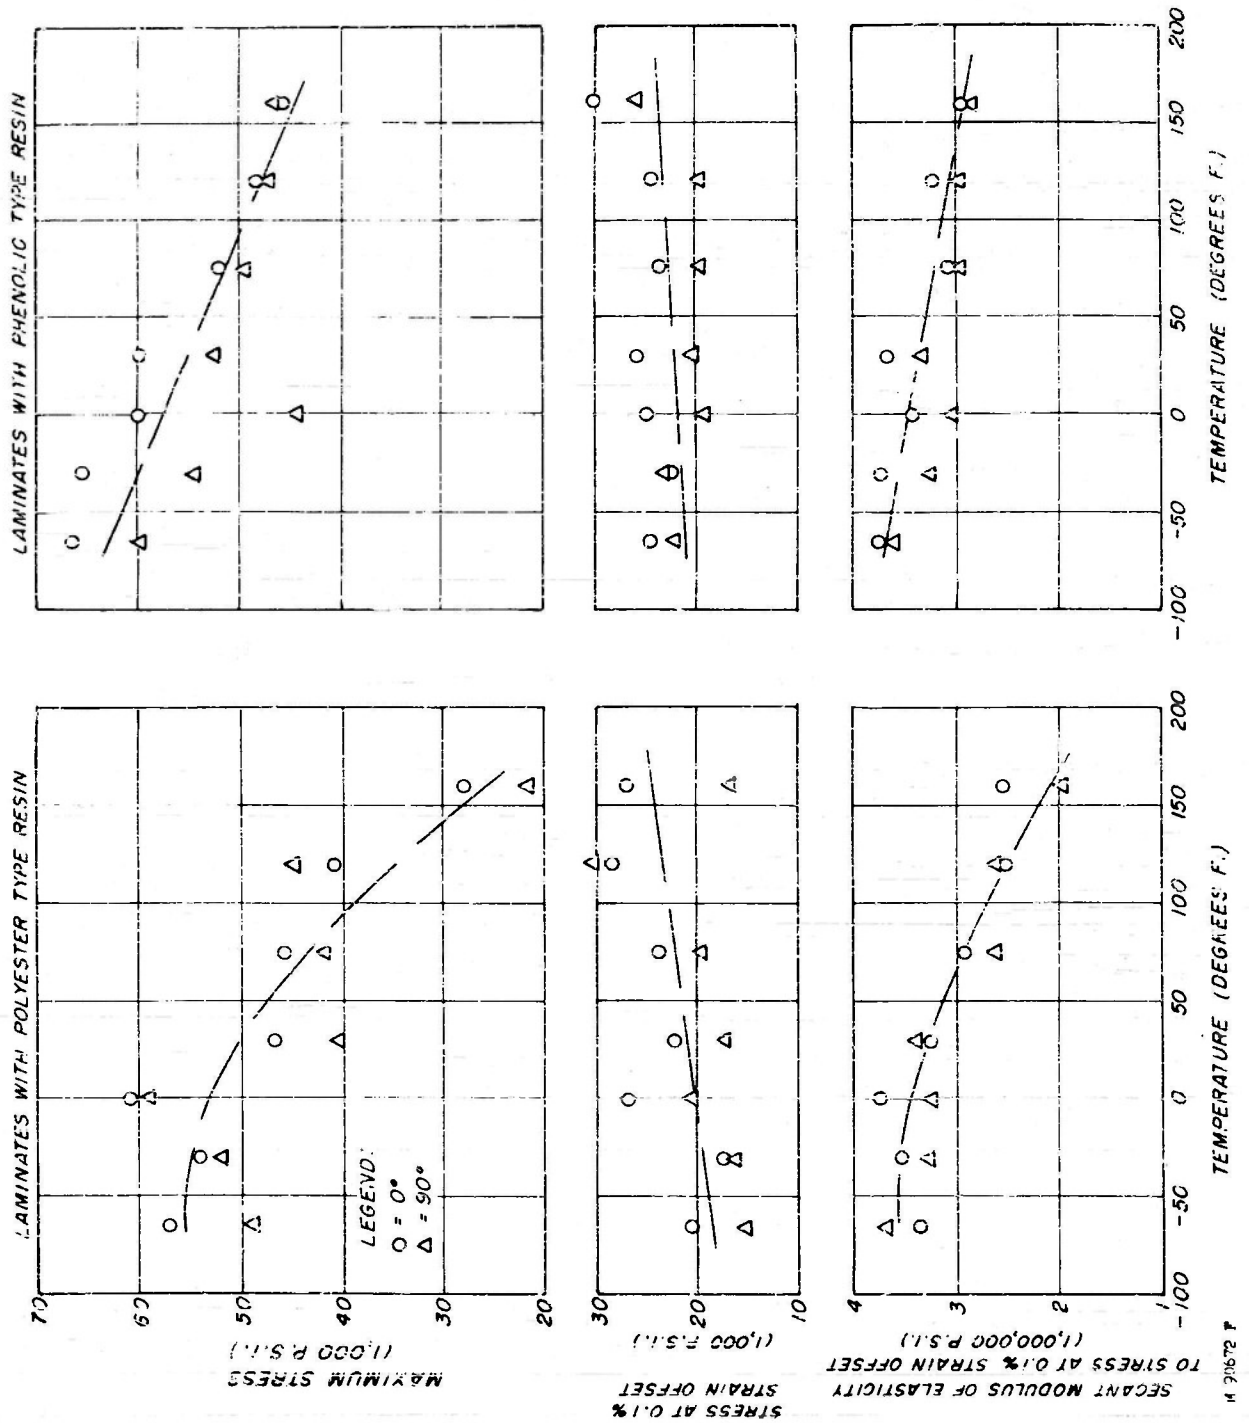




Fig. 9 Effect of Temperature at Time of Test on Flexural Properties of Plastic Laminates

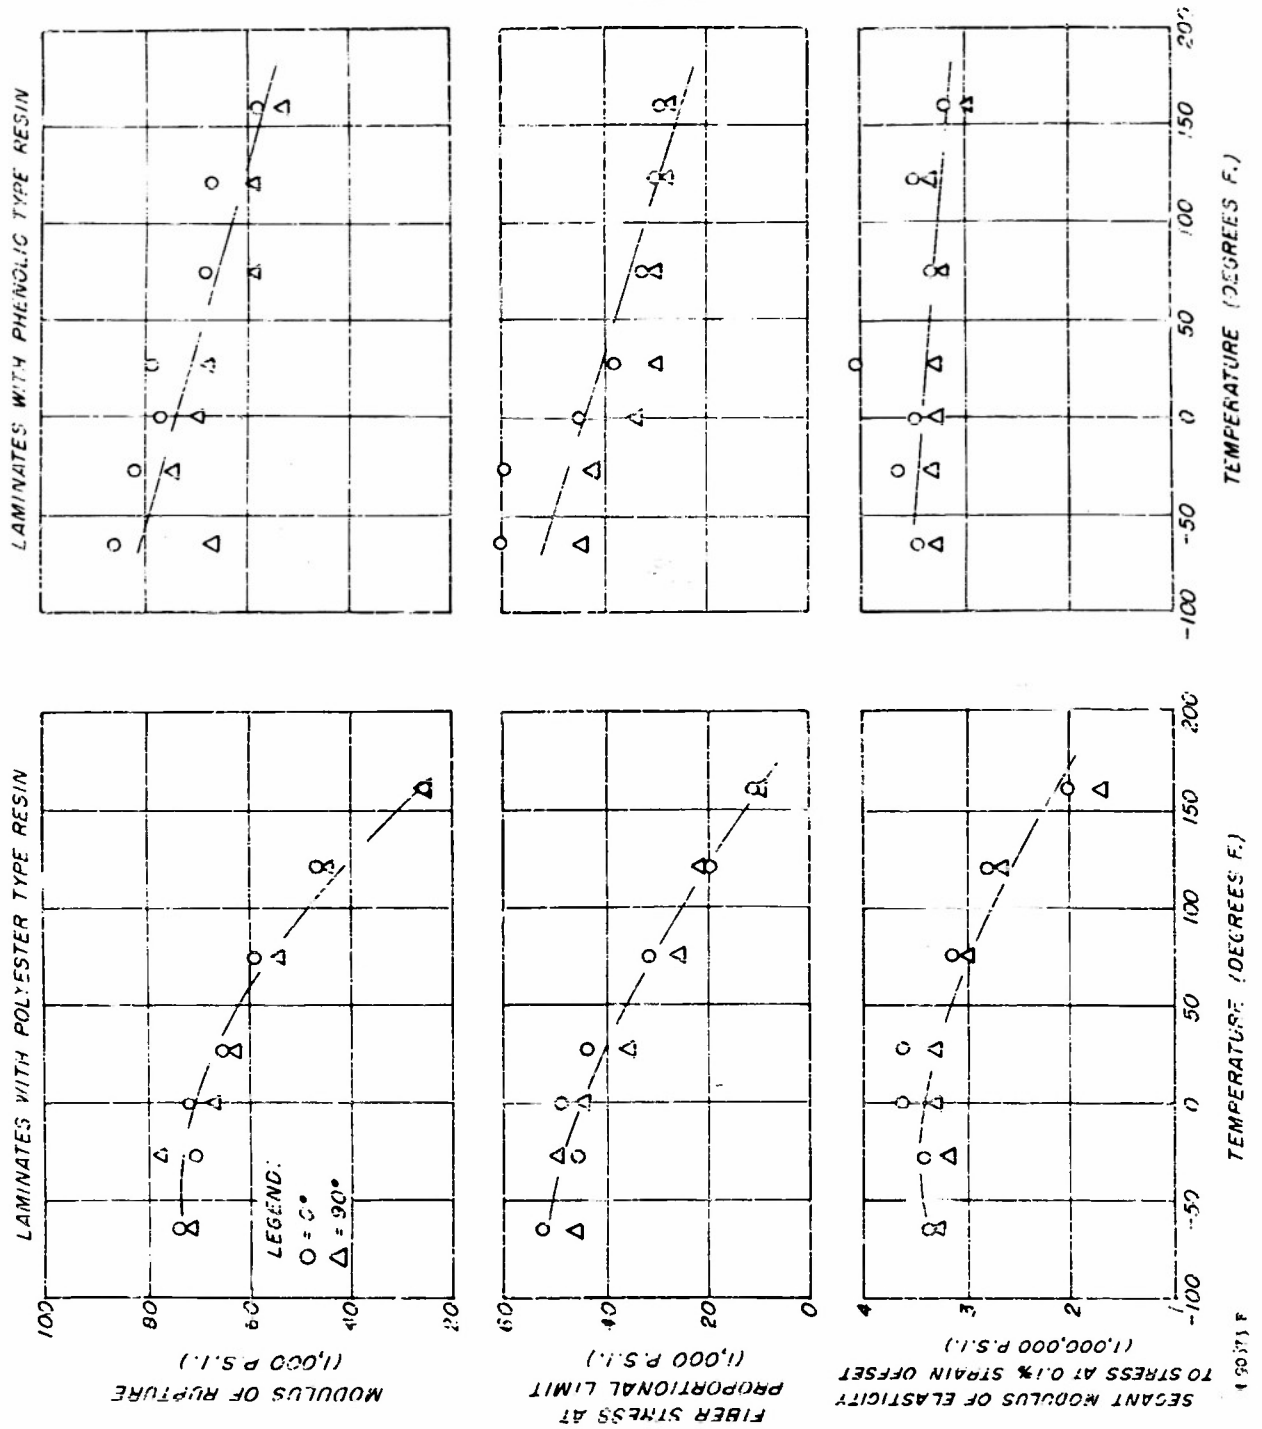
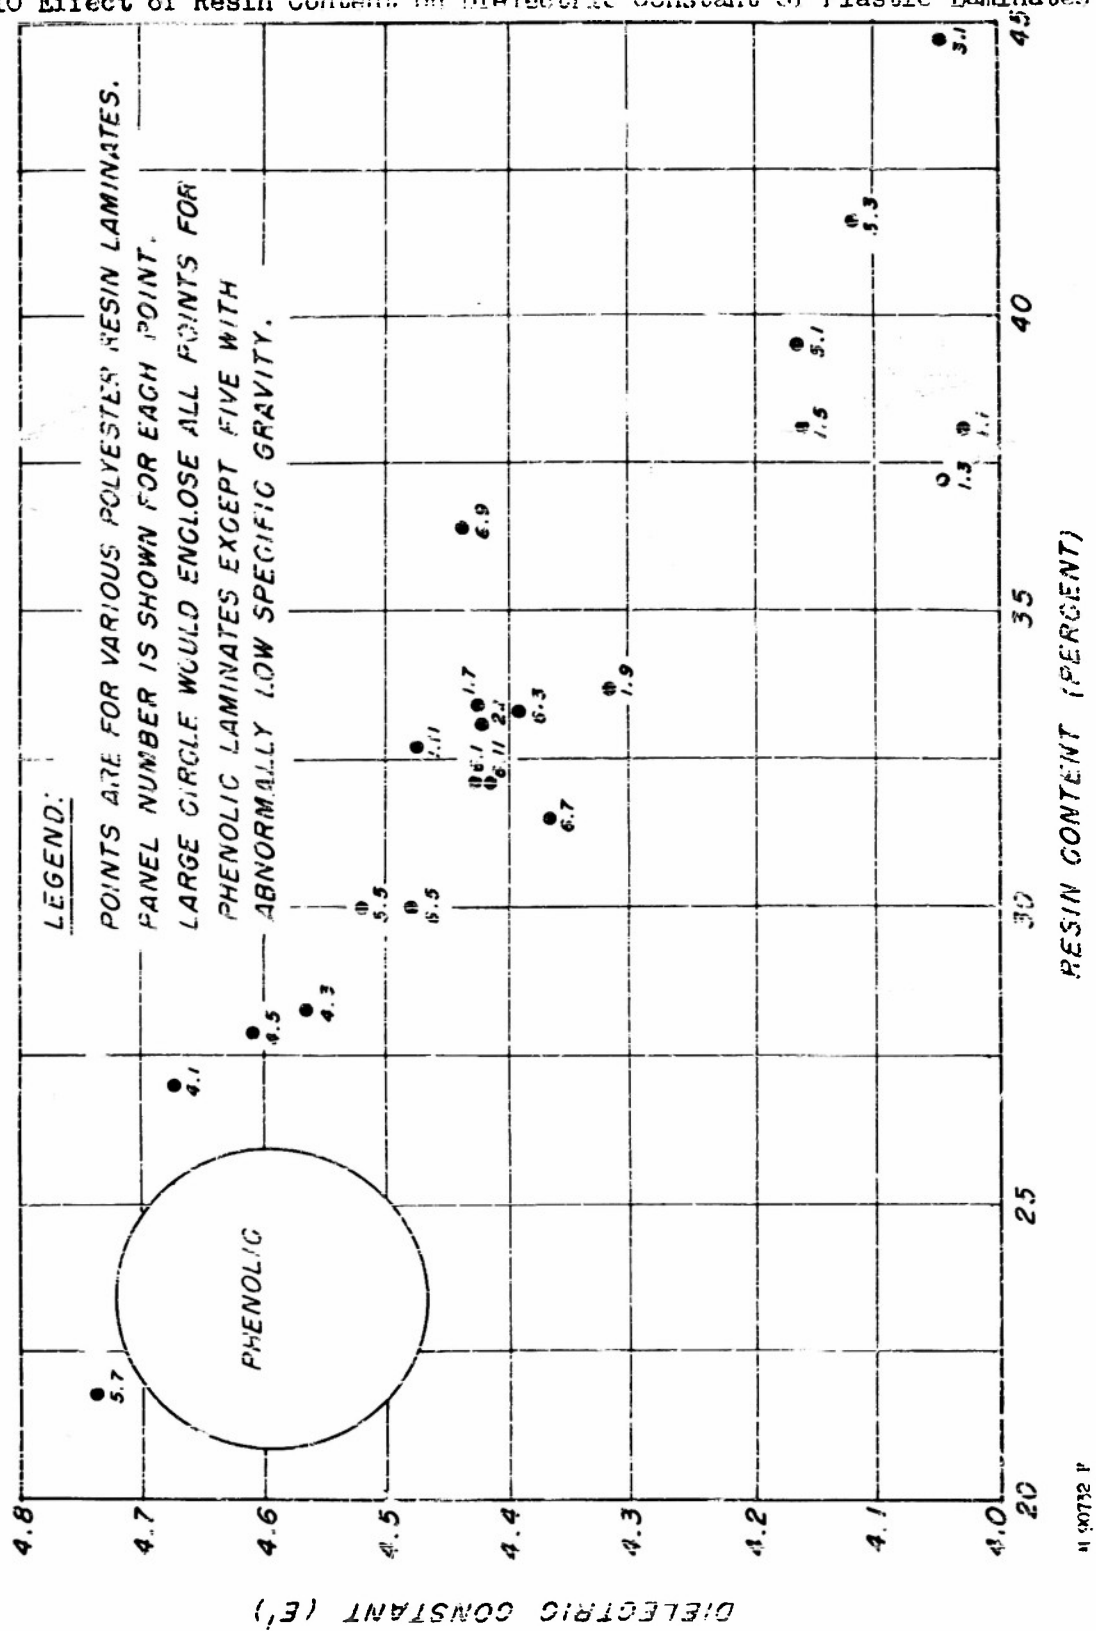


Fig. 10 Effect of Resin Content on Dielectric Constant of Plastic Laminates





# Armed Services Technical Information Agency

Because of our limited supply, you are requested to return this copy WHEN IT HAS SERVED YOUR PURPOSE so that it may be made available to other requesters. Your cooperation will be appreciated.

# AD

# 38648

NOTICE: WHEN GOVERNMENT OR OTHER DRAWINGS, SPECIFICATIONS OR OTHER DATA ARE USED FOR ANY PURPOSE OTHER THAN IN CONNECTION WITH A DEFINITELY RELATED GOVERNMENT PROCUREMENT OPERATION, THE U. S. GOVERNMENT THEREBY INCURS NO RESPONSIBILITY, NOR ANY OBLIGATION WHATSOEVER; AND THE FACT THAT THE GOVERNMENT MAY HAVE FORMULATED, FURNISHED, OR IN ANY WAY SUPPLIED THE SAID DRAWINGS, SPECIFICATIONS, OR OTHER DATA IS NOT TO BE REGARDED BY IMPLICATION OR OTHERWISE AS IN ANY MANNER LICENSING THE HOLDER OR ANY PERSON OR CORPORATION, OR CONVEYING ANY RIGHTS OR PERMISSION TO MANUFACTURE OR SELL ANY PATENTED INVENTION THAT MAY IN ANY WAY BE RELATED THERE TO.

Reproduced by

DOCUMENT SERVICE CENTER

KNOTT BUILDING, DAYTON, 2, OHIO

# UNCLASSIFIED